

Universidade do Minho

[CI-32]

Neto, S.A.D., Farias, M.M., **Pais, J.C.**, Pereira, P.A.A., Picado-Santos, L.G.


“Behavior of asphalt-rubber hot mixes obtained with high crumb rubber contents”

Asphalt Rubber 2003 Conference, Brasilia, Brasil, 2003, p. 147-166

Asphalt & Rubber

2003

Progress
Through
Flexibility

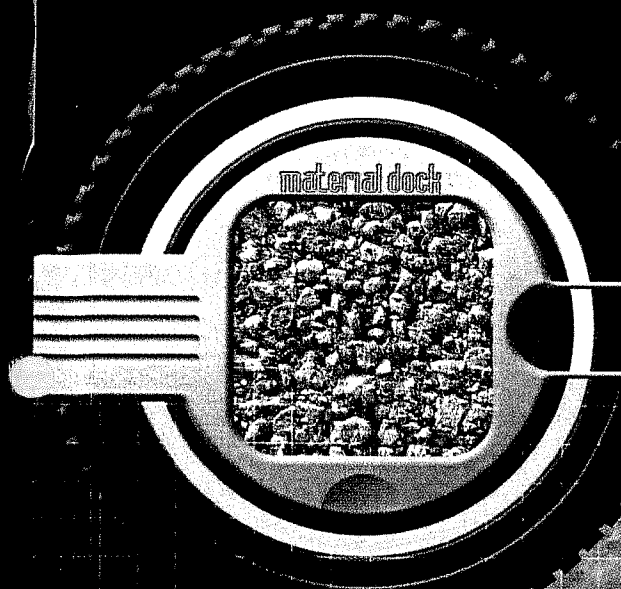

Brasilia - Brazil - Hotel Blue Tree

1st to 4th, December 2003

Proceedings

Edited by Jorge B. Sousa

Table of Contents

Part 1 - Pavement Performance and Design

THE RUBBER PAVEMENTS ASSOCIATION, TECHNICAL ADVISORY BOARD LEADING THE WAY IN ASPHALT RUBBER RESEARCH George B. Way	17
ASPHALT RUBBER MAINTENANCE TREATMENTS IN CALIFORNIA Shakir Shatnawi	35
OGFC MEETS CRM WHERE THE RUBBER MEETS THE RUBBER 15 YEARS OF DURABLE SUCCESS George B. Way	49
BITUMEN RUBBER ASPHALT: YEAR 2003 DESIGN AND CONSTRUCTION PROCEDURES IN SOUTH AFRICA C J Potgieter, J S Coetsee	65
A MECHANISTIC-EMPIRICAL BASED OVERLAY DESIGN METHOD FOR REFLECTIVE CRACKING Jorge B. Sousa, Jorge C. Pais, George B. Way	85
LONG TERM PERFORMANCE OF CRUMB RUBBER MIXTURES IN NEVADA Peter E. Sebaaly, Gabriel Bazi, Dean Weitzel, Maria Ardila-Coulson, David Bush	111

Part 2 - Mix Properties

MATERIAL CHARACTERISTICS OF ASPHALT RUBBER MIXTURES Kamil E. Kaloush, Aleksander Zborowski, Andres Sotil, George B. Way	129
BEHAVIOR OF ASPHALT-RUBBER HOT MIXES OBTAINED WITH HIGH CRUMB RUBBER CONTENTS Silvrano A. Dantas Neto, Márcio M. Farias, Jorge C. Pais, Paulo A. A. Pereira, L. Picado Santos	147
LOW-TEMPERATURE INFLUENCE IN THE PREDICTED OF PAVEMENT OVERLAY Manuel J. C. Minhoto, Jorge C. Pais, Paulo A. A. Pereira, Luís G. Picado-Santos ..	167
RUTTING PREDICTION OF ASPHALT CONCRETE AND ASPHALT RUBBER MIXTURE Mona Nourelhuda, Magdy Y. Mikhail, Michael S. Mamlouk	181
STUDIES CONCERNING THE USE OF ASPHALT RUBBER IN PORTUGAL M ^a de Lurdes Antunes, Pedro Domingos, M ^a Isabel Eusébio, Margarida Sá da Costa	195

EXPECTATION ON THE USE OF ASPHALT RUBBER IN CHILEAN PAVEMENTS
 Julio Torrejón Olmos, Luis Álvarez González and Jaime Castillo Mullor 211

ASPHALT RUBBER IN BRAZIL: PAVEMENT PERFORMANCE AND LABORATORY STUDY
 Leni Figueiredo Mathias Leite, Prepredigna de Almeida da Silva, Guilherme Edel, Laura Goretti da Motta, Luis Alberto Herrmann do Nascimento 229

ASPHALT PAVING ON STEEL STRUCTURAL BRIDGE USING CRUMB RUBBER ADDITIVE
 Wang Xu-dong, Huang Wen-yuan, Yang Zhi-feng 247

CRACKING RESISTANCE OF ASPHALT RUBBER MIX VERSUS HOT-MIX ASPHALT
 Michael Mamlouk and Barzin Mobasher 261

EVALUATION OF RUBBER MODIFIED ASPHALT CONCRETE
 Arieh Sidess and Jacob Uzan 279

Part 3 - Binder Properties

PROPERTIES OF ASPHALT-RUBBER BINDERS RELATED TO CHARACTERISTICS OF THE INCORPORATED CRUMB RUBBER
 Silvrano A. Dantas Neto, Márcio M. Farias, Jorge C. Pais, Paulo A. A. Pereira, L. Picado Santos 297

EFFECTS OF MIXING TIME AND TEMPERATURE ON THE VISCO-ELASTIC PROPERTIES OF ASPHALT RUBBER BINDER
 H. Barry Takallou, Mojie B. Takallou, 311

RHEOLOGY OF BITUMEN-RUBBER
 A COMPARATIVE STUDY OF TWO BINDERS AND TWO BINDER/FILLER SYSTEMS
 A.F. Burger, M.F.C. van de Ven, K.J. Jenkins 325

COMPARATIVE ANALYSIS OF BITUMEN – RUBBER BINDER AND POLISH STANDARD BITUMEN PROPERTIES
 Radziszewski P., Kalabinska M., Pilat J. 337

PERFORMANCE AND ACCEPTABILITY CRITERIA FOR CRUMB RUBBER MODIFIED BINDERS WITH SAME PERFORMANCE GRADED (PG) RATING
 Gajanan S. Natu, Akhtarhusein A. Tayebali 347

THE INFLUENCE OF CRUDE SOURCE AND PENETRATION GRADE ON THE INTERACTION OF CRUMB RUBBER AND BITUMEN
 Gordon Airey, Mujibur Rahman, Andrew Collop 375

Part 4 - Functional Properties

MEASUREMENT OF TIRE/PAVEMENT NOISE SOUND INTENSITY METHODOLOGY
 Paul R. Donovan, Bruce C. Rymer 399

ANALYSIS OF TRAFFIC NOISE BEFORE AND AFTER
PAVING WITH ASPHALT-RUBBER
Douglas D. Carlson, Han Zhu, Can Xiao 413

DEVELOPMENT OF ARIZONA'S QUIET PAVEMENT
RESEARCH PROGRAM
Larry Scofield, Paul R. Donavan 429

Part 5 - Recycling, trial sections and environmental aspects

2002 ASPHALT RUBBER TRIALS IN ALBERTA CANADA
B.C.M. Pulles, L.B. Treleaven, H. Soleymani, A. Schulz,
H. Donovan, R. Horton, C. McMillan 455

RECYCLING OF ASPHALT RUBBER PAVEMENTS
Mang Tia, Byron E. Ruth 473

STACK EMISSIONS WITH ASPHALT RUBBER A SYNTHESIS OF STUDIES
Don Stout, Douglas D. Carlson 485

SOCIOECONOMIC AND ENVIRONMENTAL ANALYSES FOR THE USE OF
RUBBERIZED ASPHALT IN THE CONSTRUCTION OF HIGHWAYS
Marcus Vinicius Q. Curry, Aurélio L. S. Murta,
Luis H. Figueiredo, Luis Claudio S. Montenegro 501

Part 6 - Chip seals with Asphalt Rubber

MAINTENANCE AND REHABILITATION STRATEGIES
UTILIZING ASPHALT RUBBER CHIP SEALS
Jack Van Kirk 515

BITUMEN RUBBER CHIP AND SPRAY SEALS AS
USED IN SOUTH AFRICA
C J Potgieter 531

DESIGN METHOD FOR BITUMEN
RUBBER SINGLE STONE SEALS
Dr Wynand A van Wyngaard 549

ASPHALT - RUBBER
STRESS ABSORBING MEMBRANE
STRESS ABSORBING MEMBRANE INTERLAYER
Jeffrey R. Smith 559

Part 7 - Evaluations on Materials Containing Crumb Rubber

ESTABLISHMENT OF AN ASPHALT-RUBBER
TECHNOLOGY SERVICE (ARTS)
Serji N. Amirkhanian 577

EFFECTS OF MIXING TIME AND TEMPERATURE ON THE VISCO-ELASTIC
PROPERTIES OF ASPHALT RUBBER BINDER
H. Barry Takallou, Mojie B. Takallou 589

<p>LABORATORIAL EVALUATION OF TIRE RUBBER USE AS HOT MIX AGGREGATE Luciano Pivoto Specht, Jorge A. Pereira Ceratti, Ilda Paludo</p>	<p>603</p>
<p>AN ITALIAN RESEARCH ON MECHANICAL PROPERTIES OF ASPHALT WITH TIRE RUBBER Gaetano Di Mino, Paola Tripodi</p>	<p>615</p>
<p>PERFORMANCE OF ASPHALT-RUBBER HOT MIX OVERLAYS AT BRAZILIAN HIGHWAY Luis Severo, Paulo Ruwer, Fernando Pugliero Gonçalves, Jorge Augusto Pereira Ceratti, Armando Morilha</p>	<p>633</p>
<p>EFFECT OF STORAGE TIME ON RHEOLOGICAL PROPERTIES OF CRUMB RUBBER MODIFIED BITUMEN E. Fantó, R. Durgó, Sz. Bíró, L. Bartha, Gy. Deák</p>	<p>643</p>
<p>PIONIEER EXPERIENCE WITH THE APPLICATION OF GAP GRADED ASPHALT RUBBER MIXES IN SÃO PAULO, BRAZIL Rodrigo Vasconcellos Barros and Firmino Savio Vasconcellos</p>	<p>655</p>
<p>FIRST TEST SECTIONS USING BITUMINOUS MIXES WITH ADDITION OF CRUMB RUBBER FROM WASTE TIRES, FOR URBAN PAVING APPLICATIONS IN ARGENTINA Hugo Bianchetto, Mariano López, Marcela Balige, Alejandro Bisio, Fabián Schvartzer</p>	<p>669</p>
<p>MECHANICAL PROPERTIES OF ASPHALT-RUBBER MIXES USING SHALE EXTENDER OIL Adalberto Leandro Faxina, Manoel Henrique Alba Sória</p>	<p>693</p>
<p>THE EFFECT OF CRUMB RUBBER GRADATION AND BINDER-RUBBER INTERACTION TIME ON THE MECHANICAL PROPERTIES OF ASPHALT- RUBBER MIXTURES (DRY PROCESS) Jorge Henrique Magalhães Pinheiro, Jorge Barbosa Soares</p>	<p>707</p>
<p>ASPHALT RUBBER IN DRAINABLE MIXTURES. Fredy Reyes</p>	<p>719</p>
<p>THE IMPACT OF CHEMICAL MODIFICATION FOR USED TIRE RUBBER TOWARDS SKINY MIX DESIGN FOR MAINTENANCE. Mohammed Memon, Colin Franco</p>	<p>731</p>

BEHAVIOR OF ASPHALT-RUBBER HOT MIXES OBTAINED WITH HIGH CRUMB RUBBER CONTENTS

Silvrano A. Dantas Neto* — Márcio M. Farias* — Jorge C.
Pais** — Paulo A. A. Pereira** — L. Picado Santos ***

* *Pos-graduate Program in Geotechnics, University of Brasilia*
SG 12, Asa Norte, 70910-900, Brasilia, Federal District, Brazil
silvrano@unb.br
muniz@unb.br

** *University of Minho*
Department of Civil Engineering, 4800 Guimaraes - Portugal
jpais@civil.uminho.pt
ppereira@civil.uminho.pt

*** *University of Coimbra*
Department of Civil Engineering, Pólo II, 3000 Coimbra - Portugal
picsan@dec.uc.pt

ABSTRACT: *This paper shows the results of a study about the mechanical behavior of dense graded asphalt-rubber hot mixes (grading envelope C of DNER-ES 313/97) prepared with two different types of asphalt-rubber binders. These asphalt-rubber binders were obtained with penetration grade asphalt (AC 50/70) mixed with 21% and 25% of crumb rubber in weight. The rubber was recycled from unserviceable tires using the ambient grinding process. Hot mixes made with the conventional binder AC 50/70 were also studied for comparison. The mechanical behavior of hot mixes was evaluated through laboratory tests for fatigue life, permanent deformation and indirect tensile strength. The results showed that asphalt-rubber hot mixes presented better mechanical behavior for fatigue life and permanent deformation than those obtained with the straight binder.*

KEY WORDS: *asphalt-rubber, crumb rubber, asphalt hot mixes.*

1. Introduction

The experiences obtained with the use of asphalt-rubber hot mixes in several countries showed the excellent structural and functional behavior of this type of material. In general, it can be observed improvements in the fatigue life of wearing courses, reduction of maintenance costs, increase of skid resistance, and decrease of reflective cracking in overlays, besides reduction of noise levels.

Associated to the improvement of mechanical behavior of asphalt hot mixes there is also the environmental issue. Asphalt-rubber hot mixes incorporate to the conventional binder approximately 20%, in weight, of crumb rubber recycled from ground tires. Data of the Brazilian Association of Tire Industries indicates that approximately 45 million new tires are produced annually in Brazil. Besides, it is considered that about 100 million used tires are deposited in landfills, fallow lands, rivers and lakes.

The crumb rubber recycled from ground tires is composed of different constituents capable of conferring better mechanical properties to the conventional binder [HOL 00]. The rubber content incorporated to the conventional binder is one of the main factors that influence the mechanical behavior of asphalt-rubber hot mixes [NET 03]. The increase of the rubber content produces a substantial increase in the viscosity of binders modified with crumb rubber recycled from ground tires. This increase of viscosity reduces the workability of the modified binders limiting, in general, the rubber contents to 21%, in weight.

The objective of this paper is to study the influence of the increase of rubber content incorporated to conventional binders on the mechanical behavior of asphalt-rubber hot mixes. Asphalt-rubber hot mixes obtained with dense gradation (grading envelope C of DNER-ES 313/97) were made with two different types of asphalt-rubber binders. Modified binders were produced, mixing straight asphalt of penetration grade 50/70 (AC 50/70), produced in Portugal, and crumb rubber obtained by the ambient grinding process, for rubber contents of 21% and 25%, in weight. The evaluation of the mechanical behavior of the asphalt-rubber hot mixes was made through laboratory tests for indirect tensile strength, resilient modulus, fatigue life and permanent deformation.

2. Objectives

The objective of this paper is to study of the influence of the increase of rubber content incorporate to the conventional binder on the mechanical behavior of asphalt-rubber hot mixes, in terms of indirect tensile strength, fatigue life and resistance to development of permanent deformations.

3. Background

The use of binders modified with crumb rubber recycled from ground tires in asphalt hot mixes began in the 40's. The objective of the incorporation of the crumb rubber to conventional binders was to improve the mechanical behavior of the asphalt hot mixes and to reduce environmental pollution levels [MOH 00].

In the 60's, engineer Charles McDonald began the studies about the incorporation of crumb rubber to the conventional binder, denominated as asphalt-rubber. The method of production of the asphalt-rubber was patented then and known as McDonald process or wet process [WAY 00].

In 1964, Arizona Department of Transportation (ADOT) began to use asphalt-rubber hot mixes in maintenance services, mainly in seal coat in deteriorated pavements. From 1968 to 1972, the ADOT executed a series of chip seals using asphalt-rubber. From 1974 to 1989, asphalt-rubber hot mixes were applied in several highways as Stress Absorbing Membrane Interlayer (SAMI), with the objective of reducing reflective cracks in the pavements [WAY 00].

In the 80's, asphalt binders modified with crumb rubber recycled from ground tires began to be used in chip seals and overlays executed in South Africa [VIS 00] [POT 00]. Currently, asphalt-rubber hot mixes have been executed with open, gap and dense gradation. The results showed that the asphalt-rubber hot mixes have superior fatigue life when compared with asphalt hot mixes executed with conventional binders.

3.1. Asphalt-rubber production

Modified binders with crumb rubber recycled from ground tires are obtained through the incorporation of crumb rubber to conventional binders under certain temperature conditions. The resulting asphalt-rubber presents the mechanical properties of the conventional binder and the elasticity of the crumb rubber [HUA 00].

There are two methods for the manufacture of asphalt-rubber denominated wet process and dry process. In the wet process, the conventional binder is heated up to temperatures about 190°C, in a super-heating tank in hermetic conditions, being transported soon after to an adapted mixture tank. In the mixture tank, crumb rubber is added to the preheated conventional binder. The digestion process, which is the mixture of the conventional binder with the crumb rubber, takes place over a period of 1 to 4 hours, under a temperature of 190 °C. This mixture process is assisted by the action of a horizontal single shaft in-line paddle agitator [VIS 00].

In the dry process, dry particles of crumb rubber are added into preheated aggregate, before the addition of conventional binder [VIS 00]. The aggregate is heated up to

temperatures of approximately 200 °C, then the crumb rubber is added and the mixture proceeds for approximately 15 seconds until the formation of a homogeneous composition of aggregate-crumb rubber. Then, conventional binder is added to mixture aggregate-crumb rubber by conventional methods in a mixing plant.

In general, there is not a standard procedure for production of modified binders with crumb rubber recycled from ground tires [ANT 00] [OLI 00] [VIS 00] [MOH 00] [HUA 00]. There is no fixed criterion for the choice of the content and type of crumb rubber, or for the time and temperature of digestion. These parameters are sometimes chosen in function of the production capability of the available equipments in different countries and they influence directly the behavior of the modified binders.

3.2. Mechanical properties of asphalt-rubber hot mixes

The structural performance of the wearing courses of flexible pavements is directly related to the mechanical properties of the asphalt hot mixes employed. Sousa et al. [SOU 00] studied the behavior of dense graded asphalt-rubber hot mixes made with modified binders, in terms of fatigue life and resistance to reflective cracks. Mixtures made with asphalt-rubber, for a rubber content of 18% in weight, and conventional binders presented an optimum binder content of 8% and 5%, in relation to the total mixture, respectively. The fatigue tests were carried under controlled strain, as well as under controlled stress.

The results for tests under controlled strain and controlled stress showed that asphalt-rubber hot mixes had a fatigue life superior to those mixtures made with conventional binders. This behavior is attributed to the larger flexibility of the mixtures provided by the incorporation of crumb rubber into the conventional binder [SOU 00].

Several works indicate a satisfactory performance of asphalt-rubber hot mixes in terms of resistance to the development of permanent deformations, in relation those asphalt hot mixes obtained with conventional binders [ANT 00].

4. Materials

4.1. Crumb rubber and conventional binder

Crumb rubber used in this work was recycled from ground tires using the ambient grinding process. Approximately 20% of truck tires and 80% of car tires of different types and origins were used in the crumb rubber fabrication process. The crumb rubber particles diameter varies between 0,5 to 2,0 mm. Figure 1 shows the grain size distribution curves for the crumb rubber samples and the grading envelope specified by Arizona Department of Transportation (ADOT), described in Table 1.

Table 1. Grain size distribution of crumb rubber samples and grading envelope specified by Arizona Department of Transportation (ADOT)

Sieve size		% Passing		
Inch	mm	ADOT		Rubber
N° 4	4,75	100	100	100
N° 8	2,36	100	100	99,9
N° 10	2,00	100	100	96,8
N° 16	1,18	65	100	47,7
N° 30	0,60	20	100	18,7
N° 50	0,30	0	45	7,5
N°200	0,075	0	5	0

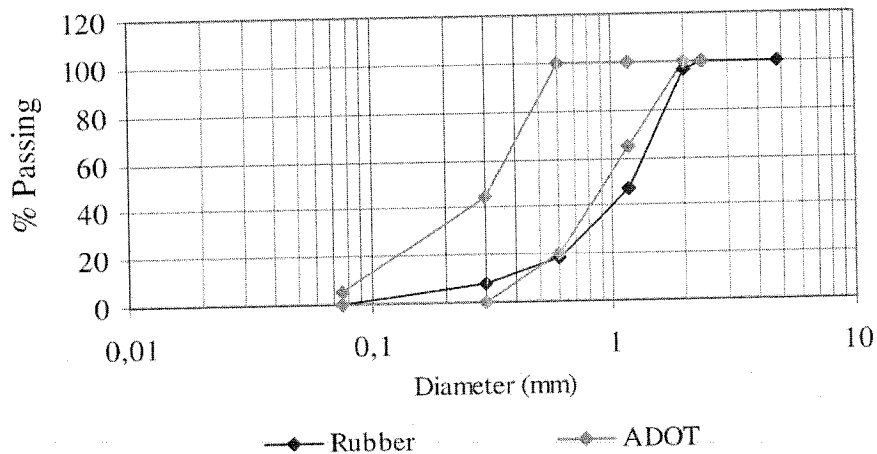


Figure 1. Grain size distribution curves for crumb rubber samples

Table 2 presents the results of physical properties characterization tests of the conventional binder AC 50/70.

Table 2. Characterization of conventional binder AC 50/70

Physical properties	AC 50/70
Penetration, ASTM D 5-95 (1/10 mm)	52,0
Softening point, ASTM D36-97 (°C)	50,6
Brookfield viscosity at 175°C, ASTM D 4402-87 (cP)	87,5
Resilience, ASTM D5329 (%)	14,0

4.2. Aggregates

The following mineral aggregates were used for producing the asphalt hot mixes studied in this paper:

- Grade 1 crushed granitic stone: particle size 11 - 16 mm;
- Grade 0 crushed granitic stone: particle size - 11 mm;
- Fine crushed granitic aggregate: particle size < 4 mm.

Granitic filler, available in the Laboratory of Pavements of the University of Minho in Portugal, was also used. The aggregate mixture presents a dense graded curve specified by DNER-ES 313/97 as grade envelope C.

Table 3 shows the aggregate mixture composition to comply with the specified grain size distribution. Some results of aggregate characterization tests are also shown. Table 4 presents the grain size distribution of the aggregates used in the asphalt hot mixes and the theoretical values for the designed mixture.

Figure 2 presents the grain size distribution curves of the specified grade envelope and of the theoretical mixture designed for the asphalt hot mixes according to the aggregate mixture composition described in Table 3.

Table 3. *Characterization of aggregates used in the asphalt hot mixes*

Physical properties	Crushed stone 1	Crushed stone 0	Fine aggregate	Filler
Aggregate percentage (%)	10	30	55	5
Apparent specific gravity (kN/m ³)	2,641	2,584	2,520	2,520
Specific gravity of grains (kN/m ³)	2,696	2,680	2,710	2,710
Water absorption (%)	0,77	1,39	-	-

Table 4. *Grain size distribution of the aggregates and of the dense graded mix*

Sieve size		Percentagem passando em peso						
Inch	mm	Grade envelope C		Crushed stone 1	Crushed stone 0	Fine aggregate	Filler	Mix
¾"	19,1	100	100	100	100	100	100	100
½"	12,5	85	100	89,55	100	100	100	98,2
3/8"	9,5	75	100	41,02	97,45	100	100	89,4
Nº 4	4,8	50	85	3,45	24,57	99,81	100	65,9
Nº 10	2,0	30	75	1,09	4,18	76,36	100	47,3
Nº 40	0,425	15	40	0,83	2,04	35,04	99,17	24,1
Nº 80	0,18	8	30	0,70	1,59	16,56	93,96	13,6
Nº 200	0,075	5	10	0,53	1,13	6,18	75,03	6,9

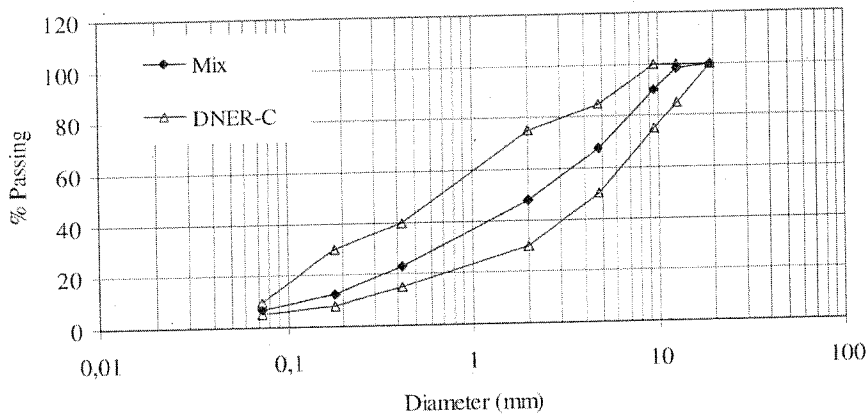


Figure 2. Grain size distribution curves for dense graded mix

5. Asphalt hot mixes: design and production

5.1. Modified binders used in the asphalt-rubber hot mixes.

The following modified binders configurations were chosen for the study of the mechanical behavior of the dense graded asphalt-rubber hot mixes:

- Asphalt-rubber 1 (AR-1): straight binder AC 50/70 + 21% of crumb rubber, digestion time of 300 minutes and digestion temperature of 210°C;
- Asphalt-rubber 2 (AR-2): straight binder AC 50/70 + 25% of crumb rubber, digestion time of 300 minutes and digestion temperature of 210°C;

The use of these asphalt-rubber configurations allows evaluating the mechanical behavior of asphalt-rubber hot mixes made with modified binders obtained with rubber content higher than 21%, in weight. Hot mixes were also prepared with the straight binder AC 50/70 in order to compare with the mechanical properties of mixes with modified binders. Table 5 presents the physical properties of the modified binders used in the asphalt-rubber hot mixes.

The digestion time of 300 minutes was chosen due the high initial Brookfield viscosity presented by the modified binder with a rubber content of 25%, in weight. The modified binders with rubber contents above 21% present high initial Brookfield viscosity, mainly in the first 120 minutes of digestion. The increase of the digestion time produces a decrease of the modified binders viscosity due to the softening of the rubber particles [NET 03].

5.2. Design and production of conventional and asphalt-rubber hot mixes

Marshall method was used for the determination of the optimum binder content of the asphalt hot mixes. Table 6 presents the values of temperatures of the binders, of the

aggregates and of compaction of the asphalt hot mixes obtained with AC 50/70, AR-1 and AR-2 binders. These temperatures values were chosen taking in consideration the workability of the asphalt-rubber binders and the experience of local producers in application of this type of material.

Table 5. *Characterization of binders AR-1, AR-2 e AC 50/70*

Physical properties	AR-1	AR-2	AC 50/70
Penetration, ASTM D5 (1/10 mm)	23,0	24,5	52,0
Resilience, ASTM D5329 (%)	39,0	48,0	14,0
Softening point, ASTM D36 (°C)	89,8	96,6	50,6
Brookfield Viscosity at 210°C, ASTM D 4402 (cP)	4280	8000	-

Table 6. *Temperatures used in the production of conventional and asphalt-rubber hot mixes*

Temperatures	AC 50/70	AR1/AR2
Binder heating (°C)	160	170
Aggregates heating (°C)	177	190
Compaction of the mix (°C)	160	164

The dense graded mixture made with the conventional binder AC 50/70 presented an optimum binder content of 7,05%, in relation to the total weight of the mixture, and a void content of 4,5%, as described in Table 7. The mix design of the dense graded asphalt-rubber hot mixes indicated an optimum binder content of 9,61%. However, for these bitumen contents the volumetric parameters of the mixes obtained were different.

The mechanical behavior of asphalt hot mixes depends, among other factors, of their volumetric properties, as for example, the void content. Thus, for the mixtures made with the asphalt-rubber AR-1 and AR-2, the optimum binder content of 9,61% in total weight was used, but with a void content of 4,5%. In this way, it is guaranteed that all asphalt hot mixes presented the same volumetric parameters, and the type of binder is the only variable affecting the mechanical behavior of the mixes. Table 7 presents the volumetric parameters of the specimens of asphalt hot mixes used in the mechanical tests.

Table 7. *Properties of the dense graded asphalt hot mixes studied*

Mix properties	AC 50/70	AR-1/AR-2
Apparent density (g/cm ³)	2,249	2,251
Void content (%)	4,5	4,5
Void in the mineral aggregate – VMA (%)	19,3	19,2
Void filled with asphalt binder – VFA (%)	76,7	76,7
Optimum binder content (%)	7,05	9,61

After the mix design, several specimens of asphalt hot mixes with AC 50/70, AR-1 and AR-2 binders were prepared. A mechanical device with production capability of 50 kg of asphalt mixture was used to accomplish the mixture between the mineral aggregates and asphalt binders. Compaction of the asphalt hot mix was performed in a metallic mold with dimensions (7,3 x 49,2 x 75,2 cm), and a vibratory wheel roller was used to achieve the apparent density of the asphalt hot mixes defined in the design.

An asphalt concrete slab is obtained, from which specimens were extracted to be used in indirect tensile strength, resilient modulus, fatigue life and permanent deformation tests. The slab and an specimen is shown in Figure 3.

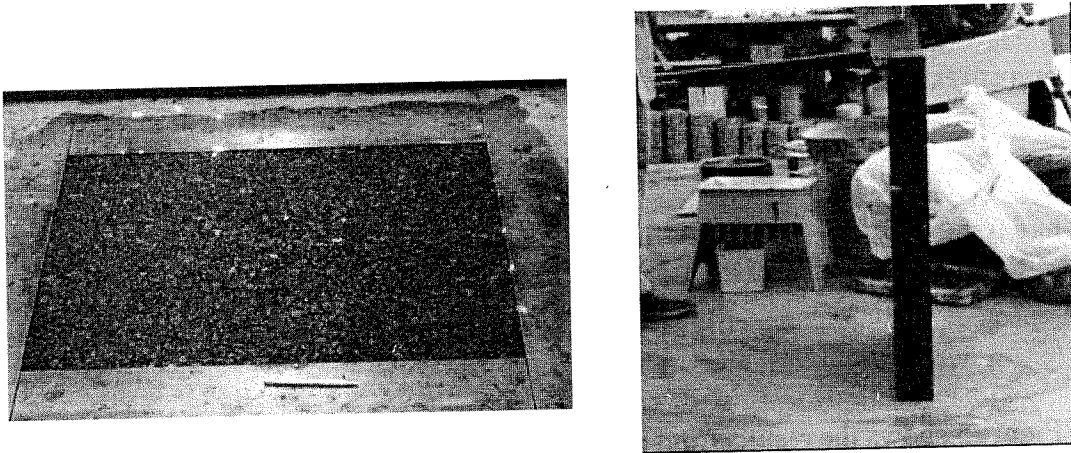


Figure 3. Compacted asphalt hot mixes slabs and specimen for mechanical tests

6. Asphalt hot mixes: tests, results and discussion

6.1. Indirect tensile strength tests

The indirect tensile test is carried out through the application of a vertical force F in the diametrical plan of the specimen until failure [MED 97]. The indirect tensile strength is calculated by Equation 6.1, as a function of the geometric characteristics and of the maximum vertical load applied diametrically to the specimen.

$$\sigma_t = \frac{2F}{\pi t \phi} \quad (6.1)$$

Where:

- σ_t : indirect tensile strength;
- F : maximum vertical load applied;
- t : height of the specimen;
- ϕ : diameter of the specimen

Indirect tensile tests were carried out at a temperature of 20°C, on specimens submitted to an aging process at 85°C for 5 days in an oven. Non-aged specimens were also tested for comparison. This laboratory aging process, normalized by AASHTO PP2/94, simulates the long-term aging that occurs in asphalt hot mixes in field. The tests were carried out in accordance with the recommendations of DNER-ME 138/94 standard. Figure 4 shows a picture of a specimen at the moment of failure during the indirect tensile test

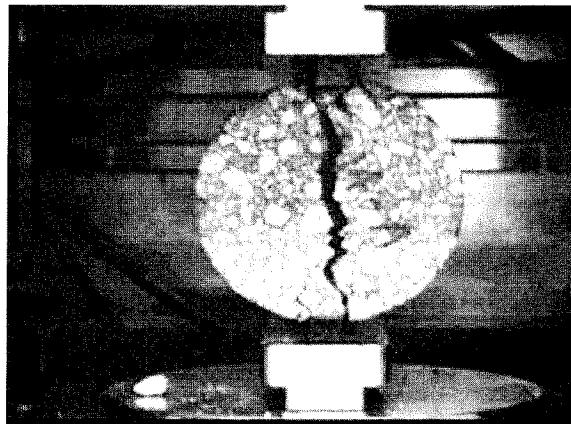


Figure 4. *Indirect tensile test*

Figure 5 shows the results from indirect tensile tests for the dense graded asphalt hot mixes made with AC 50/70, AR-1 and AR-2 binders. The aging process produced an increase in the indirect tensile strength of the dense graded asphalt hot mixes due to the increase of binder stiffness. For specimens submitted to the aging process, the results show that the dense graded asphalt-rubber hot mixes present indirect tensile strength slightly (10%) lower than those obtained for conventional asphalt hot mixes with AC 50/70 binder. By comparing, the results of the dense graded asphalt hot mixes obtained with asphalt-rubbers AR-1 and AR-2, it is verified that the increase of rubber content incorporated to the conventional binder produces a slight decrease in the indirect tensile strength. However, the differences in tensile strength in all cases were not significant.

6.2. Resilient modulus, phase angle and fatigue life tests

The resilient modulus of asphalt hot mixes is defined as the ratio between the tensile stress applied to the specimen and the tensile strain produced. This value depends on several factors such as intensity, frequency and time of load application. In this paper the values of resilient modulus of the asphalt hot mixes will be presented for different load application frequencies

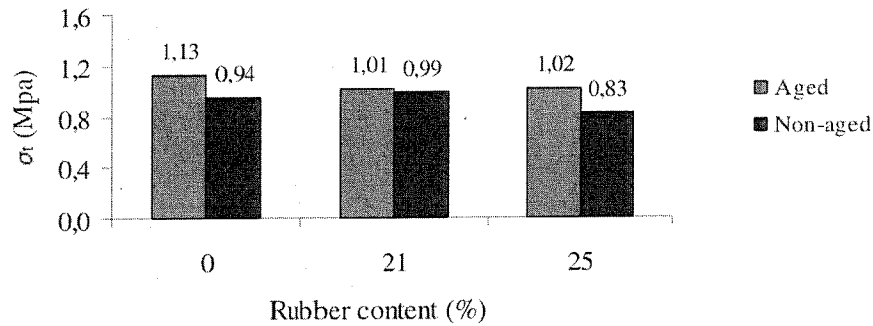


Figure 5. Indirect tensile strength of the dense graded asphalt hot mixes

The fatigue life of asphalt hot mixes in controlled strain tests is defined as the number of load applications (N) that reduces by 50% the initial stiffness of the specimen.

The phase angle is calculated as a function of the time lag between the application of a certain load F and the displacement produced in the specimen. Therefore, the phase angle, calculated by Equation 6.2, is a quantitative measure of elastic capacity of the constituent material of the specimen

$$\phi = 360 f.t \tag{6.2}$$

where:

- ϕ: phase angle, in degrees (°);
- t: time lag between F and δ, in seconds (s).
- f: load frequency, in Hertz (Hz);

The resilient modulus and fatigue life tests were carried out under controlled strain conditions in beam specimens of bituminous concrete with the following dimensions: 381 ± 6,35 mm in length, 50,8 ± 6,35 mm in height and 63,5 ± 6,35 mm in width, as showed in Figure 6. Figure 7 shows the load application system device used for performing resilient modulus and fatigue life tests. These tests are normalized by AASHTO TP8/96 standard.

Table 8 presents the conditions imposed during resilient modulus and fatigue life tests. The specimens obtained from asphalt hot mixes made with AC 50/70, AR-1 and AR-2 binders were submitted to the long-term aging process described previously, and normalized by AASTHO PP2/94.

Table 8. Load application conditions for resilient modulus and fatigue life tests

Test Parameters	Fatigue life	Resilient modulus
Temperature of specimen test (°C)	20	20
Load frequency (Hz)	10	10; 5; 2; 1; 0,5; 0,2; 0,1

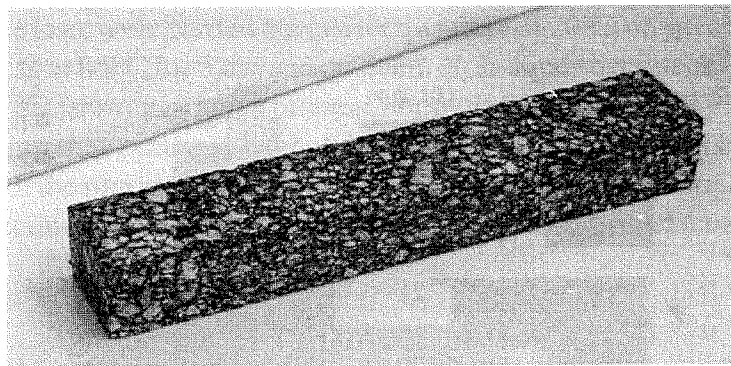


Figure 6. *Specimen for resilient modulus and fatigue life tests*

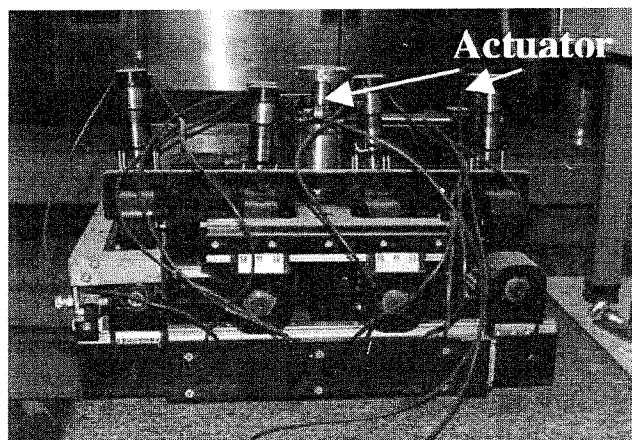


Figure 7. *Lateral view of the system of load application in resilient modulus and fatigue life tests*

Figure 8 presents the results from resilient modulus tests of the specimens obtained from dense graded asphalt hot mixes with AC 50/70, AR-1 and AR-2 binders. The results show the variation of the resilient modulus with the frequency of load application. Figure 9 presents the results of phase angle of the asphalt hot mixes studied, as a function of the load application frequency.

The results presented in the Figure 8 shows that the increase of rubber content produces a decrease in the values of resilient modulus of the asphalt hot mix made with the asphalt-rubber AR-2 in relation to those produced with the asphalt-rubber AR-1 and with the conventional binder AC 50/70. The decrease of the values of resilient modulus indicates an increase of the flexibility

Figure 9 shows that the values of phase angles of the asphalt hot mix made with asphalt-rubber AR-1 are lightly lower than those of the asphalt hot mixes made with the asphalt-rubber AR-2 and with the conventional binder AC 50/70, but significant

differences can not be observed. The asphalt-rubber hot mix made with AR-2, which presents 25% in weight of incorporated crumb rubber, presents the same values of phase angles as the asphalt hot mix made with conventional binder AC 50/70.

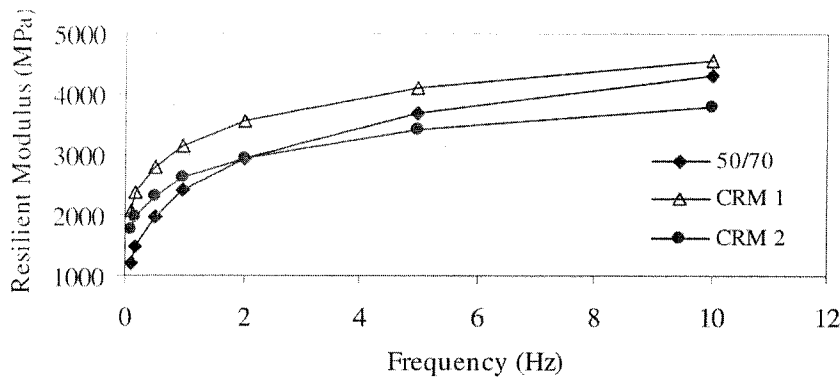


Figure 8. Resilient modulus of the dense graded asphalt hot mixes

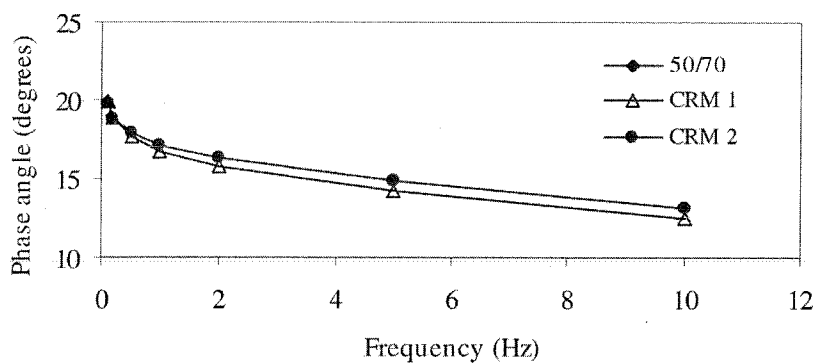


Figure 9. Phase angles of the dense graded asphalt hot mixes

Figure 10 presents the results of fatigue life tests of asphalt hot mixes made with the AC 50/70, AR-1 and AR-2 binders. The results are expressed as a function of a parameter denominated α_{rubber} and defined by Equation 6.3. This parameter represents the relationship between the fatigue life of the asphalt-rubber hot mix and the fatigue life of the mixture made with the conventional binder, for each tensile strain induced in the specimen

$$\alpha_{\text{rubber}} = \frac{N_{\text{ARHM}}}{N_{\text{AHM}}} \quad (6.3)$$

Where:

N_{ARHM} : fatigue life of the asphalt-rubber hot mix;

N_{AHM} : fatigue life of the conventional asphalt hot mix.

This parameter measures the gain or loss of fatigue life of the asphalt-rubber hot mixes in relation to the conventional mixtures. For the conventional mixtures, taken as reference, α_{rubber} values will always be equal to one.

During fatigue life tests, tensile strains of 400 and 800 microns were induced in the bituminous concrete beam specimen. The results presented in Figure 10 show that the asphalt-rubber hot mixes made with the AR-1 and AR-2 binders present a fatigue life superior to conventional asphalt hot mix, for the tensile strains induced in the specimens. The increase of the rubber content for 25% still produces an increase in the fatigue life of the mixture made with the asphalt-rubber AR-2 in relation to the mixture obtained with the AR-1 binder. The gain in fatigue life was approximately 50% for AR-1 and 150% for AR-2 for a tensile strain of 800 microns, representing a heavy traffic of vehicles. For lower traffic, represented by a tensile strain of 400 microns, the fatigue life results are available only for mixes with AR-1 and indicate a gain in fatigue life above four times

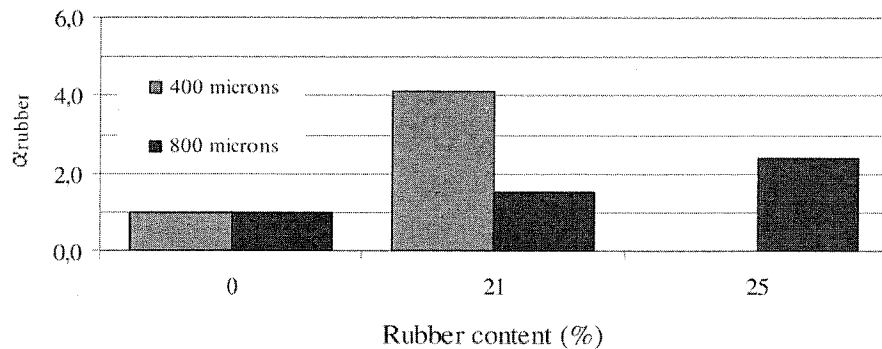


Figure 10. *Fatigue life of dense graded asphalt hot mixes*

The analysis of the overall results of indirect tensile strength, resilient modulus, phase angle and fatigues life tests of the studied asphalt hot mixes, shows that the incorporation of rubber contents of up to 25% produces an improvement in the elastic properties of these mixtures. This improvement of elastic properties represents an increase of elasticity, flexibility and reflective cracking strength of the asphalt hot mixes

6.3. Permanent deformation of the asphalt hot mixes studied

In general, rutting (permanent deformations) in pavements occurs initially due to a densification of the bituminous layers in the first load cycles, and later through the plastic shear strains produced in the bituminous layers. This plastic shear strains cause a displacement of the material of the bituminous layer without volumetric variation forming upheaval zones adjacent to the wheel paths [SOU 94].

Based on several works, the Strategic Highway Research Program (SHRP) established

a procedure to evaluate rutting in pavements through the evaluation of the evolution of the plastic shear strains that occurs in asphalt hot mixes. The main assumption of this procedure it is that rutting is the result of a phenomenon of plastic shear flow under constant volume of the mixture, caused by the shear stress produced below the edge of the truck tires [SOU 94].

The determination of plastic shear strains is made by means of the repeated simple shear test at constant height (RSST-CH). This test consists of applying to a cylindrical specimen with 15 cm of diameter and 5 cm of thickness, shown in Figure 11, a repeated shear stress, while measuring the produced plastic shear strains, in a desired controlled temperature.

The RSST-CH is executed using a horizontal and a vertical mechanical actuator. The horizontal actuator controls the magnitude of the applied shear stress; while the vertical actuator guarantees that specimen is tested in a controlled stress condition, maintaining the constant height along of the test. Table 9 presents the conditions imposed during RSST-CH tests. The temperature of 50°C is typically used for pavements in Portugal, while the higher temperature of 60°C was adopted to simulate more severe climates as in Brazil.

Table 9. Test conditions for RSST-CH

Test Parameters	Values
Temperature of the specimens (°C)	50 and 60 ± 0,5
Shear stress actuating on the specimens (kPa)	69 ± 5
Loading time (s)	0,1
Unloading time (s)	0,6

The RSST-CH test is carried out until the specimen reaches the maximum plastic shear strain of 0,04545, which is equivalent to the limit value of 12,7 mm for the rut depth in the wheel path. Equation 6.4 presents the law of evolution of the plastic shear strain (γ_p) with the number of applied load cycles in the RSST-CH.

$$\gamma_p = a.N^b \tag{6.4}$$

Where:

γ_p : plastic shear strains measured in the specimen during RSST-CH;

a, b: laboratory parameters;

N: number of applied load cycles to the specimen during RSST-CH.

The rut depth in the wheel path can be estimated from plastic shear strains measured in the RSST-CH. Equation 6.5 shows a relationship between the rut depth and the plastic

shear strains in the RSST-CH [SOU 94].

$$\delta_{\text{rut depth}} = 279,40 \cdot \gamma_p \quad (6.5)$$

Where:

$\delta_{\text{rut depth}}$: rut depth in the wheel path, in mm;

γ_p : plastic shear strain measured in the specimen during RSST-CH.

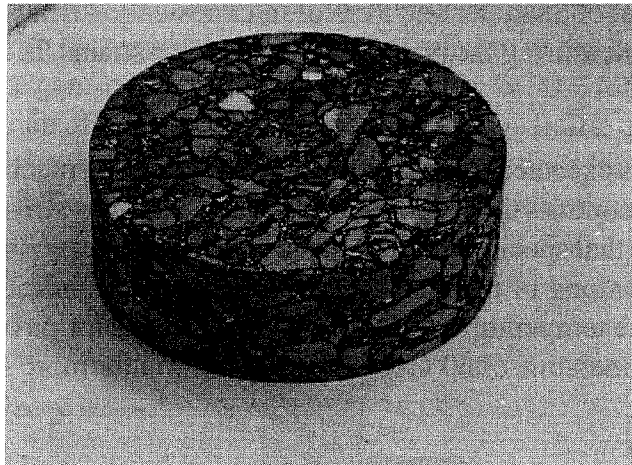


Figure 11. *Cylindrical specimen used in the RSST-CH*

Equation 6.6 shows the relationship between the number of passes of the equivalent standard axle load of 82 kN ($ESAL_{\text{mrd}}$) as a function of the number of applied load cycles in the RSST-CH (N_{mpss}) for the specimen to reach the maximum plastic shear strain of 0,04545.

Where:

$ESAL_{\text{mrd}}$: number of cycles of the equivalent standard axle load of 82 kN correspondent to the maximum rut depth of 12,7 mm;

N_{mpss} : number of applied load cycles in the RSST-CH for the specimen to reach the maximum plastic shear strain of 0,04545.

Figure 12 shows the results of the RSST-CH tests for the asphalt hot mixes made with the AC 50/70, AR-1 and AR-2 binders and test temperatures specified in Table 9. The results are expressed in terms of number of cycles of the equivalent standard axle, calculated by Equation 6.6, for the mixture to reach the maximum plastic shear strain or a limit rut depth of 12,7 mm.

The results show that the asphalt-rubber hot mixes made with the AR-1 and AR-2 binders present larger resistance to the development of the plastic shear strains than the conventional asphalt hot mixes made with AC 50/70 binder, for both test temperatures

used. For the temperature of 50°C, mixes made with AR-1 and AR-2 resisted, respectively, three times and two times more cycles to suffer the limit rut depth when compared with mixes prepared with the conventional binder. For 60°C, the gain was of 1,3% and three times, respectively, for mixes with binders AR-1 and AR-2.

This improvement of the behavior of the asphalt-rubber hot mixes occurred due to the larger elastic recovery of AR-1 and AR-2 binders in relation to the conventional binder AC 50/70, during the RSST-CH tests. The RSST-CH test temperatures of the asphalt-rubber hot mixes are well below the values of softening points for AR-1 and AR-2 binders shown in Table 5. Therefore, the elastic component of the binders AR-1 and AR-2 prevails in the behavior of the asphalt hot mixtures during the RSST-CH tests, resulting in larger resistance to the development of plastic shear strains.

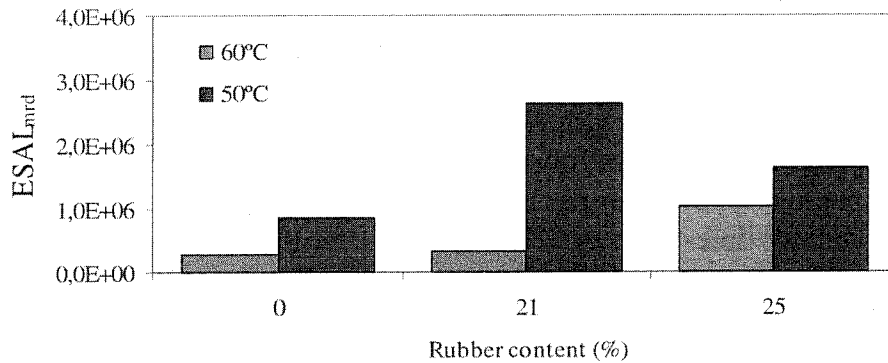


Figure 12. Results of RSST-CH tests for dense graded asphalt hot mixes

For the conventional asphalt hot mixes, the softening point of the conventional binder AC 50/70 is practically equal or inferior to the test temperatures used. Therefore, this binder is already in a quite viscous state, presenting little resistance to the development of the plastic shear strains.

For the test temperature of 60°C, the increase of the rubber content incorporated to conventional binder of 21% to 25% caused an increase in the resistance to the development of the plastic shear strains. However, for the test temperature of 50°C, the resistance to plastic shear strains of the asphalt hot mixes made with the asphalt-rubber AR-2 decreased in relation to mixture obtained with the asphalt-rubber AR-1.

The elevation of the test temperature had a greater impact of hot mixes made with AR-1 binder due to its lower softening point when compared with AR-2, as shown in Table 5

7. Conclusions

The incorporation of the crumb rubber recycled from ground tires to conventional binders produces a slight reduction in the indirect tensile strength of the asphalt-rubber

hot mixes, in relation to those made with the conventional binders. The aging process produced a slight increase of tensile strength for all mixes investigated. However, the difference in tensile strength was not significant when compared to other aspects, such as fatigue life and rutting resistance.

The results of resilient modulus and of the phase angle values showed that an increase of rubber content produces an improvement in the elastic properties of the asphalt hot mixtures studied. This improvement of the elastic properties was reflected in the increase of the life of fatigue of the asphalt-rubber hot mixes, in relation to the conventional mixtures. The gain in fatigue life was approximately 50% for AR-1 and 150% for AR-2 with a tensile strain of 800 microns, representing a heavy traffic of vehicles. For lower traffic, represented by a tensile strain of 400 microns, gain in fatigue life above four times were observed in mixes with AR-1.

The mixtures made with the asphalt-rubber AR-1 and AR-2 presented larger resistance to the permanent deformations, obtained in repeated simple shear test at constant height (RSST-CH), than those made with AC 50/70 binder. This increase of the resistance to the permanent deformations was observed for the test temperatures of 50°C and 60°C. For the temperature of 50°C, mixes made with AR-1 and AR-2 resisted, respectively, three times and two times more cycles to suffer the limit rut depth when compared with mixes prepared with the conventional binder. For 60°C, the gain was of 1,3 and three times, respectively, for mixes with binders AR-1 and AR-2.

The softening point can be defined as the temperature above which the binders behave as a viscous fluid. The asphalt hot mixes made with the asphalt-rubber AR-1 and AR-2 were tested at typical temperatures, which are below the softening point of these binders.

The asphalt hot mixes made with AC 50/70 were tested at temperatures equal or superior to the softening point this binder. However, for the test temperatures used, asphalt-rubber AR-1 and AR-2 were more viscous, with higher elasticity, and consequently more resistant to development of the plastic shear strains than the mixtures made with the conventional binder AC 50/70.

The production of asphalt-rubber binders with rubber contents up to 25% was only possible due to the decrease of the specific surface of the crumb rubber recycled used in the experiments. For this purpose, it was necessary to use crumb rubber with particle dimensions larger than that those usually acceptable in the specifications of crumb rubber for use in asphalt-rubbers. The crumb rubber used in this work presented a grain size distribution slightly out of the specifications of ADOT.

However, the results of the mechanical tests performed in the asphalt-rubber hot mixes made with the modified binder obtained with the crumb rubber used in this work showed that the increase of the rubber particles size produces an improvement in the elastic properties of the asphalt hot mixes, and also in their behavior at high temperatures by the increase of the resistance to development of ruts.

8. Acknowledgements

This work is part of the doctoral research program at Pos-graduate Program in Geotechnics of the University of Brasilia and with support of the Department of Civil Engineering of the University of Minho, in Portugal. It is supported with grants from CAPES (Coordenação de Aperfeiçoamento de Pessoal de Nível Superior) and CNPQ (Conselho Nacional de Desenvolvimento Científico e Tecnológico). The authors are also thankful to the companies that supplied the materials used in this work, among them Cepsa (supplier of the binders), Biosafe (supplier of the granulated rubber) and Bezerras LTDA (supplier of the mineral aggregates).

9. References

- [ANT 00] ANTUNES M.L, BAPTISTA F., EUSÉBIO M.I., COSTA M.S., MIRANDA C.V., "Characterization of Asphalt Rubber Mixtures for Pavement Rehabilitation Projects in Portugal", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p.285-307.
- [HOL 00] HOLLERAN G., REED J.R., "Emulsification of asphalt rubber blends", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 383-409.
- [HUA 00] HUANG P., YAN J., "Research on the Properties and Technology of Crumb Rubber Asphalt Mixture", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 331-340.
- [MED 97] MEDINA J., "Mecânica dos Pavimentos", Editora: UFRJ, Rio de Janeiro, Brasil, 1997, 380p.
- [MOH 00] MOHAMMAD L.N., HUANG B., ROBERTS F., RASOULIAN M., "Accelerated loading performance and laboratory characterization of crumb rubber asphalt pavements", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 189-220.
- [NET 03] DANTAS NETO S.A., FARIAS M.M., PAIS J.C., PEREIRA A.A., "Optimization of Asphalt Rubber Hot Mixes Based on Performance Laboratory Tests", Third International Symposium on Maintenance and Rehabilitation of Pavements and Technological Control, Guimaraes, Portugal, 2003.
- [OLI 00] OLIVER J.W.H., "Rutting and fatigue properties of crumbed rubber hot mix asphalts", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 221-240.
- [POT 00] POTGIETER C.J., SADLER D.E., VILLIERS E.M., "Bitumen Rubber Asphalt Experiences in the Republic of South Africa", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 73-96.

- [SOU 00] SOUSA J.B, PAIS J.C., SAÏM R., "The Effect of Mode of Loading on the Comparison Between Asphalt Rubber and Traditional Hot Mixes Laboratory Performance", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 259-272.
- [SOU 94] SOUSA J.B, SOLAIMANIAN M., WEISSMAN S.L., "Development and Use of the Repeated Shear Test (Constant Height): An Optional Superpave Mix Design Tool", Strategic Highway Research Program, National Research Council, Washington, 1994, 96p.
- [VIS 00] VISSER A.T., VERHAEGHE B., "Bitumen rubber: Lessons learned in south Africa", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 33-52.
- [WAY 00] WAY G.B., "OFGC meets CRM: where the rubber meets the rubber", Asphalt Rubber 2000 – Proceedings, Portugal, 2000, p. 15-32.