

# Studies on the mouldability of structural foams in hybrid moulds

A. A. Nogueira

*Vangest Group, Marinha Grande, Portugal*

P. T. Gago

*3DTech, Lda, Marinha Grande, Portugal*

P. G. Martinho

*Polytechnic Institute of Leiria, School of Technology and Management, Leiria, Portugal*

A. M. Brito

*Dep. Polymer Engineering, University of Minho, Guimarães, Portugal*

A. S. Pouzada

*Institute for Polymer and Composites/I3N, University of Minho, Guimarães, Portugal*

**ABSTRACT:** In the context of the research project *Hybridmould 21*, studies on the mouldability of structural foams using hybrid moulds have been carried out. Hybrid injection moulds are an increasingly considered alternative for prototype series or short production runs of large dimension parts. In this solution for injection moulds the moulding elements (blocks or other inserts) are manufactured in alternative metallic materials or in synthetic materials typically using rapid prototyping techniques.

Structural foams, known since the 70s, are moulded by injection moulding without using the high pressures typically used in injection moulding. The formation of the structural foam results from the dispersed gaseous phase, which derives from the expansion of a chemical blowing agent usually compounded in a compatible masterbatch. In this project various thermoplastics and thermosets were used, namely, PP, ABS and PUR, using a hybrid mould instrumented for the monitoring of temperature, pressure and expansion force. The moulding block was manufactured by vacuum casting of an epoxy composite. In this paper are mainly discussed the results obtained on liquid injection moulding polyurethane resins in the hybrid mould.

## 1 INTRODUCTION

The highly competitive modern market, the low life cycles of the products and the short time to market are the main challenges for the industries. The companies need to reduce costs and manufacturing times (Martinho et al. 2005; Oliveira and Pouzada 2001). For some industries (e.g. automotive and electronic), the search of alternative solutions/methodologies for design and manufacture of tools for prototype or short production series of plastics parts lead to consider the resource offered by rapid prototyping and tooling (RPT) techniques and non-conventional manufacturing techniques (Pontes et al. 2005).

Vacuum casting is a RPT process that allows manufacturing soft tools using epoxy composites. The resins are poured, in vacuum, over the master to reproduce a moulding block with accuracy and good surface finishing (Dunne et al. 2004). The main advantage of this process is the short time to obtain freeform moulding blocks in comparison to conventional machining. In this way, it is possible to reduce the cost of comparable conventional tools by 40% and the lead time to 2 to 5 weeks (Canevarolo 2004; Pontes et al. 2010). Generally, epoxy resins filled with metallic powder (usually aluminium) are used

to improve thermal and mechanical properties (Vasconcelos et al. 2006). Thus, the vacuum casting is ideal for quick manufacturing of the moulding blocks used in the hybrid moulds (Bareta et al. 2006).

The hybrid mould concept was developed to attend the new demands of the market for shortest time-to-market and lower costs. These moulds combine a structure manufactured conventionally and moulding blocks produced by RPT (typically vacuum casting). Thus, hybrid moulds are a good solution for prototype series and short production series (Martinho et al. 2005; Pouzada 2009).

Hybrid moulds are made with materials with thermal and mechanical properties different from steel which leads to longer processing cycles and requiring less strength demanding injection pressures (Martinho et al. 2008a; Martinho et al. 2008b). Therefore, moulding processes involving low processing pressure, namely injection moulding of structural foams and reaction injection moulding (RIM) are ideal to be used with hybrid moulds.

Structural foams (SF) moulded by injection moulding develop a structure consisting of a low density cellular core, and a solid skin with density similar to thermoplastic. An inert gas is added at the molten thermoplastics to promote the cellular structure; chemical blowing agents (CBA) are the most

common in SF injection moulding (Kamal et al. 2009). The polymer is blended with a CBA and then a short shot is injected in the mould under controlled temperature and pressure conditions. As soon as injection ends, the blowing agent expands and the foam fills completely the impression (Lanz et al. 2002). The typical thickness of a SF is between 4 and 9 mm, the density reduction is normally 10 to 35% and the pressure in the impression is approximately 4 MPa, an order of magnitude lower than in conventional injection moulding (Malloy 1994).

RIM involves the chemical reaction between two or more liquids, allowing that the mixture and polymerization occurs inside the mould (Park and Colton 2003). The RIM process use reagents with low viscosity, which requires low pressure to fill large and complex parts. The quick filling of the impression can result in turbulent flow and formation of air bubbles. However, there are systems with fast reaction that can solidify before the complete filling, causing incomplete parts (Tomori et al. 2004). RIM is more appropriate to produce thick and large parts, with shorter cycle time. For small parts, this process is less competitive (Wohlens and Grimm 2003). The low viscosity of the raw materials and the reduced pressure during processing results in lighter and cheaper moulds, which can be manufactured in alternative materials (e.g. filled epoxy resins). Consequently RIM is usually seen as an alternative for short run and prototype series that become economically viable. The main problems of RIM are the poor surface quality and voiding, and flash in the final parts. Thus, finishing operations are frequently necessary, to a cost in the final part (Park and Colton 2003).

## 2 EXPERIMENTAL

### 2.1 The test part

The shape and main dimensions of the test part in this work are shown in Figure 1.

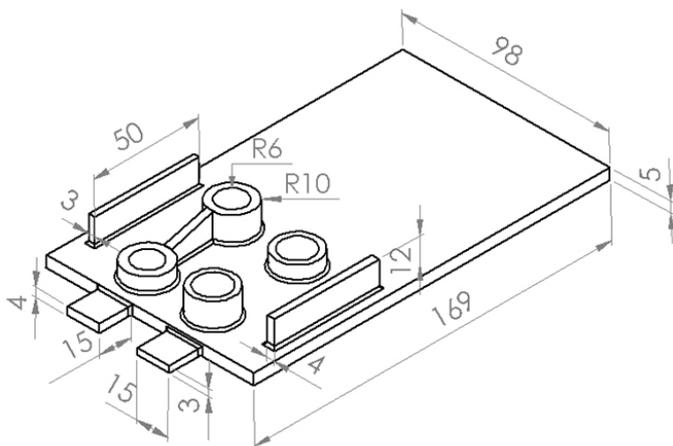


Figure 1 – Geometry and main dimensions of the plastics part.

The plastics part is 5 mm in thickness, which is typical in SF injection mouldings. The features in the part (castles, ribs and ledges) were designed to assess their processability in low pressure injection processes (SF injection moulding and RIM).

### 2.2 The tool

The tool used in this study is a hybrid mould constituted by a steel structure and a moulding block assembled in the ejection side, which was manufactured by vacuum casting. Figure 2 shows the layout of the hybrid mould.

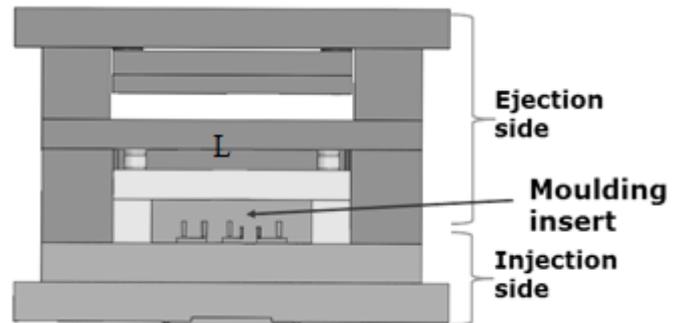


Figure 2 – Hybrid mould layout.

This mould was instrumented with one Kistler type 9204B load cell (L), one Kistler type 6157B pressure sensor (P1), and three Priamus type N 4008B temperature sensors (T1, T2 and T3).

The position of the temperature and pressure sensors on the mould surface is shown in Figure 3.

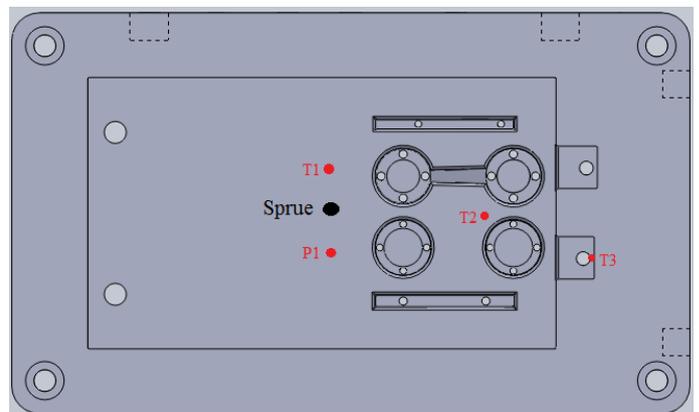


Figure 3 – Hybrid mould layout.

### 2.3 Materials

The moulding block was produced in a composite of epoxy resin (Biresin L74) filled with 60 wt% of aluminium powder. The thermal and mechanical properties of this composite as mentioned by Martinho et al. (Martinho et al. 2008a) are shown in the Table 1.

Table 1 – Properties of the epoxy composite.

Properties	Biresin L74 + 60% Al
Specific gravity	1.65 Mg.m <sup>-3</sup>
Specific heat	1279.19 J.kg <sup>-1</sup> .K <sup>-1</sup>
Thermal conductivity	0.606 W.m <sup>-1</sup> .K <sup>-1</sup>
Thermal diffusivity	0.286×10 <sup>-6</sup> m <sup>2</sup> .s <sup>-1</sup>
Coefficient of thermal expansion	6.00×10 <sup>-5</sup> K <sup>-1</sup>
Flexural modulus (20°C)	5-6 GPa

The SF mouldings were produced in two materials: polypropylene (PP) Domolen 1100N, from Domo (Belgium), and acrylonitrile butadiene styrene (ABS) Kumho 710 (Korea). CBA masterbatches, Tracel PP 2200 SP and Tracel IMC 4200 were used for PP-SF and ABS-SF, respectively.

The RIM mouldings were produced with two polyurethane (PUR) systems: Biresin RG 53, from Sika (Germany) and Daltorim ED 12160, from Huntsman (USA). The Biresin RG 53 is a compact system with density of 1.20 Mg.m<sup>-3</sup> with properties similar to PP and polyethylene (PE). The Daltorim ED 12160 is an integral foam system that allows obtaining low density mouldings (typically 0.40-0.50 Mg.m<sup>-3</sup>), especially adequate for thicker parts (4-20 mm), produced in non-metallic moulds. The main properties of these RIM systems are presented in the Table 2.

Table 2 – Properties of the RIM systems.

Parameter	Biresin RG53	Daltorim ED 12160
Density [Mg/m <sup>3</sup> ]	1.20	0.40-0.50
Pot life [s]	60	72
Demoulding time [min]	10	10
Curing time [day]	1	1

## 2.4 SF injection moulding

The mouldings were produced with a Victory Spex 50 machine (Engel, Austria). The machine was equipped with a shut-off nozzle to avoid the drooling of the melt. Two thermoregulators Piovani THN6P (Italy) were used to control the mould temperature. The monitoring signals from the sensors were acquired with a Multi Daq 8101A data acquisition system (Priamus, Switzerland).

The processing conditions were selected according to (Esteves et al. 2011) and are detailed in Table 3. To study the mouldability of the part four levels of mould filling were used in the injection of PP and three for ABS.

Table 3 – Processing conditions of SF injection moulding.

Parameter	PP	ABS
Injection temperature [°C]	230	240
Mould temperature [°C]	Core	70
	Cavity	20
Cooling time [s]	200	170
	80	85
Filling of mould [%]	85	90
	90	90
	95	95
Chemical blowing agent [wt%]	3	
	4	

The use of non-metallic materials in the moulding block (epoxy composite with lower thermal conductivity) determined the use of different temperatures in the core and the cavity sides of the mould.

The injection temperature was selected according to the materials datasheets and the decomposition temperature of the CBA masterbatch. The cooling time was determined experimentally (ejection when the moulding was sufficiently rigid for not warping).

## 2.5 Reaction injection moulding

To produce the PUR mouldings the high-pressure foam-producing CMC HP40/2P (Cosmec, Italy) RIM equipment was used.

The processing conditions (Table 4) were selected according to the datasheets of the materials and experimental studies.

Table 4 – Processing conditions of RIM process.

Parameter	Daltorim ED 12160	Biresin RG 53
Mould temperature [°C]	30	20
Resin temperature [°C]	23	23
Mixing ratio (I/P)*	1.10	0.75
Flow rate [gr/s]	100	
Mixture pressure (MPa)	ca. 18	

\*(isocyanate/polyol)

## 3 RESULTS

### 3.1 SF injection moulding

SF injection moulding is an unstable process for low levels of mould filling. For PP and at 80% of moulding filling, it was verified that the mouldings were not completely filled. For ABS, due its higher viscosity, at the same level of 80% of mould filling it was not possible to obtain complete mouldings. For higher levels of 85 and 90% the process became unstable and some mouldings are incomplete (Fig. 4).

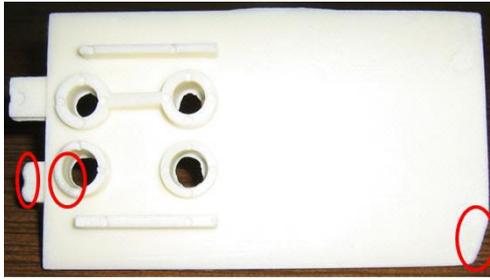


Figure 4 – ABS-SF incomplete moulding.

The use of hybrid moulds, with different materials (composite epoxy and steel) in the core and the cavity, lead to varying shrinkage over the mouldings. The thermal conductivity of steel is about  $40 \text{ W.m}^{-1}.\text{K}^{-1}$ , whereas in the epoxy composite is much lower,  $0,61 \text{ W.m}^{-1}.\text{K}^{-1}$ . Thus, very different cooling rates are set in the two mould sides.

Semi-crystalline materials as PP are more prone to warpage, because in the slower cooling side of moulding (the epoxy composite side) more crystalline structures develop. In the steel side the cooling is faster and there is not time enough for the crystalline structures fully develop. Thus, in the PP SF mouldings, due to this inhomogeneous crystalline distribution, there is more warpage. The Figure 5 shows a warped moulding.

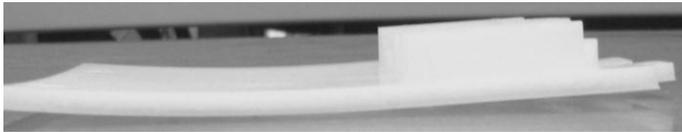


Figure 5 – Warpage in PP-SF moulding.

The successive temperature and pressure cycles, and the ejection friction leads to the degradation in the moulding surface of the epoxy composite moulding block, as shown the Figure 6.



Figure 6 – Composite moulding block after successive injection cycles.

This degradation was more noticeable after 1000 injection cycles and in the more featured zone with details.

### 3.1.1 SF injection moulding monitoring

Figure 7 shows a typical plot of pressure and clamping force during the injection cycle.

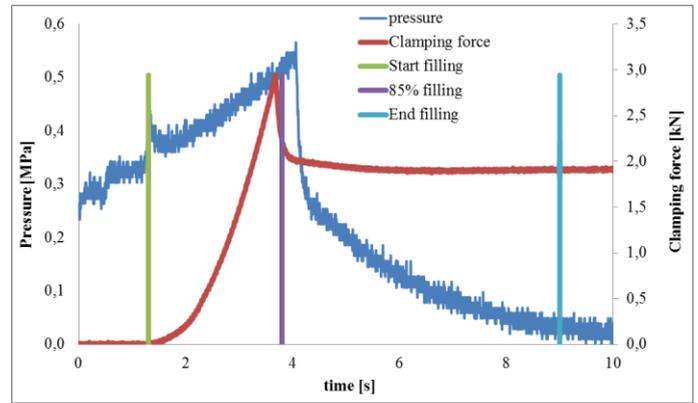


Figure 7 – Pressure and clamping force evolution in SF injection moulding.

When the injection phase starts the pressure and clamping force increase linearly until the required level of mould filling is reached. The complete filling is promoted by the CBA expansion, with significantly lower pressure and clamping force.

Due to the force in the mould resulting from the injection, there is a peak at the end of the injection phase. It drops abruptly as soon as the injection pressure is released. The clamping force remains constant until the end of the moulding cycle, while the pressure decreases linearly.

In Table 5 and Table 6 the results of the SF injection moulding monitoring are presented.

Table 5 – Impression pressure data (MPa).

% fill	3wt% CBA				4wt% CBA			
	80	85	90	95	80	85	90	95
PP	0.52	0.54	0.56	0.58	0.50	0.52	0.54	0.57
ABS	-	0.73	0.79	0.80	-	0.65	0.73	0.73

Table 6 – Clamping force data (kN).

% fill	3wt% CBA				4wt% CBA			
	80	85	90	95	80	85	90	95
PP	1.80	2.49	2.91	3.34	2.05	2.30	2.51	3.17
ABS	-	-	3.76	4.99	-	4.06	4.54	5.19

Upon increasing the level of mould filling, there is a rise in pressure and clamping force in the impression, as a result of the higher volume of material injected. Nevertheless, it is verified that the pressure and clamping force are an order of magnitude smaller than in conventional injection moulding.

### 3.2 Reaction injection moulding

In the RIM process the same hybrid mould was used, in spite of it having been designed for SF injection moulding. Consequently it is not the most suitable for RIM due to the inadequate sprue and

venting system, and it was difficult to obtain mouldings without air bubbles.

The Figure 8 shows a part produced by RIM.

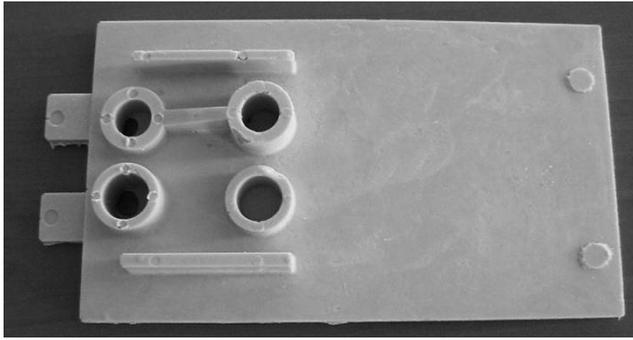


Figure 8 – PUR moulding produced by RIM.

The use of moulding blocks manufactured in non-metallic materials can cause more adhesion between the moulding insert and the part (Gonçalves et al. 2007). Thus, a silicone release agent was used to help the ejection of the moulding and increase the life time of the tool. In this study more than 100 parts were moulded without damaging of the moulding surface.

Fig. 9 shows the aspect of the moulding surface after being used in SF injection moulding and RIM.

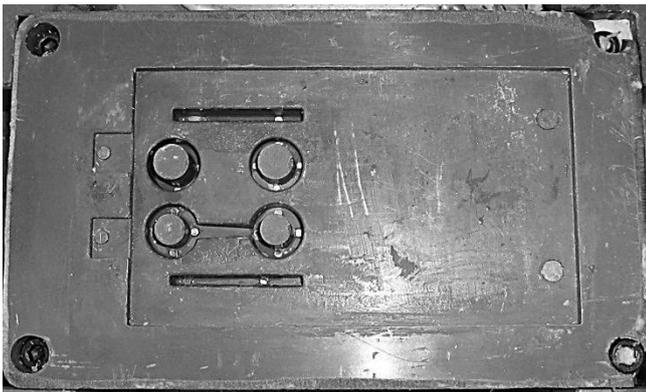


Figure 9 – Moulding surface after use in RIM processing.

RIM does not require cooling as in SF injection moulding, as the temperatures during the exothermic polymerisation reaction are relatively lower than in injection moulding. Therefore, the mouldings are less susceptible to warpage. On the other hand, as RIM involves the reaction of two liquid and produces a low crystalline and quasi-isotropic material, there is no warpage of the mouldings.

### 3.2.1 RIM monitoring

The monitoring of the temperature and pressure was performed only in the *Daltorim* mouldings. A typical plot of the temperature evolution during the process is shown in Figure 10.

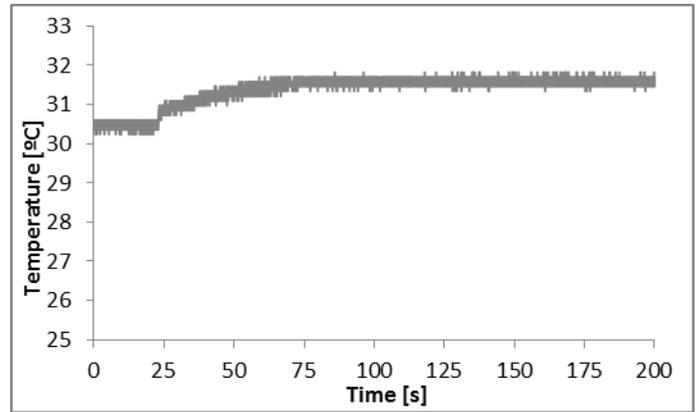


Figure 10 – Typical temperature during the RIM process.

RIM is an exothermic process that causes a slight increase of temperature in the mould.

The pressure in this system is negligible. Thus, lighter and less expensive moulds can be used.

### 3.3 SF injection moulding vs. RIM

As a result of the physical properties of the corresponding raw materials and the level of filling there is a large variation in the weights of the mouldings in the various conditions, as shown in Table 7.

Table 7 – Results of the mouldings weight.

Material	Filling [%]	Weight [g]
PP-SF	80	61.4
	85	65.3
	90	69.2
	95	73.1
ABS-SF	85	80.4
	90	84.8
	95	89.5
Daltorim ED 12160		58.3
Biresin RG 53		155.8

Compact RIM materials, as Biresin RG 53, are denser than usual thermoplastics. However, as integral foam systems (Daltorim ED 12160) it is possible to reduce approximately the weight by one third. SF injection moulding may reduce the moulding weight by 20%.

The RIM cycle time is *ca.* 600 s, longer than the SF injection moulding (*ca.* 120 s), but the moulds used in SF injection moulding can be more expensive than RIM process, which may balance the final product cost.

The RIM parts have some flash in the parting line and mould vents implying frequently the need of finishing operations.

## CONCLUSIONS

A study was conducted on the adequacy of hybrid moulds to low pressure moulding processes: structural foam injection moulding and RIM.

In the moulding of SF the adequate processing conditions (level of filling and CBA content; process temperatures) are essential to produce good undamaged parts.

In RIM the pressure and temperatures are significantly lower than in SF injection moulding. Therefore, the tools in this process may last long than in SF injection moulding.

In SF injection moulding the clamping force and impression pressure are an order of magnitude less than conventional injection moulding.

Therefore hybrid moulds are a good solution for low pressure processes, as SF injection moulding and RIM.

## ACKNOWLEDGEMENTS

The authors acknowledge the support of the program QREN 'Concessão de Incentivos Financeiros no âmbito do Sistema de Incentivos à Investigação e Desenvolvimento Tecnológico' for funding the contract 2010/013307 – Project Hybridmould 21.

## REFERENCES

- Bareta, D. R., Zeilmann, R. P., Costa, C. A. & Pouzada, A. S. 2006. Application of alternative materials in hybrid mould cores. In *RPD 2006 - Building the future by innovation; Proc. Int. Conf., Marinha Grande, Portugal, November*.
- Canevarolo, S. V. 2004. "Técnicas de Caracterização de Polímeros." Artliber, São Paulo, 430.
- Dunne, P., Soe, S. P., Byrne, G., Venus, A. & Wheatley, A. R. 2004. Some demands on rapid prototypes used as master patterns in rapid tooling for injection moulding. *Journal of Materials Processing Technology* **150**: 201-207.
- Esteves, F. R., Pouzada, A. S. & Martins, C. I. 2011. Formulation and characterization of polypropylene structural foam for large parts. In *6th Int Materials Symposium - 15º Enc. Soc. Port. Mat.; Proc. Int. Conf., Guimarães, Portugal, April*.
- Gonçalves, M. W., Salmoria, G. V., Ahrens, C. H. & Pouzada, A. S. 2007. Study of tribological properties of moulds obtained by stereolithography. *Virtual and Physical Prototyping* **2** (1): 29-36.
- Kamal, M. R., Isayev, A. I. & Liu, S.-J. 2009. *Injection Molding - Technology and Fundamentals*, Munich: Carl Hanser Verlag.
- Lanz, R. W., Melkote, S. N. & Kotnis, M. A. 2002. Machinability of rapid tooling composite board. *Journal of Materials Processing Technology* **127** (2): 242-245.
- Malloy, R. A. 1994. *Plastic part design for injection molding: An introduction*, New York: Hanser Publishers.
- Martinho, P., Bártolo, P. J., Queirós, M. P., Pontes, A. J. & Pouzada, A. S. 2005. Hybrid Moulds: the Use of Combined Techniques for the Rapid Manufacturing of Injection Moulds. In P. J. Bártolo (ed.), *Virtual Modelling and Rapid Manufacturing - Advanced Research in Virtual and Rapid Prototyping*: 421, London: Taylor and Francis.
- Martinho, P. G., Cardon, L., Neves, T., Bártolo, P. J. & Pouzada, A. S. 2008a. On the influence of the materials used on the moulding blocks of hybrid moulds. In *PMI 2008 - Int. Conf. on Polymers & Moulds Innovations; Proc. Int. Conf., Ghent, Belgium, September*.
- Martinho, P. G., Cardon, L., Neves, T., Bártolo, P. J. & Pouzada, A. S. 2008b. A study of the ejection forces on moulding inserts obtained by RPT techniques. In *RPD 2008 - Designing the Industry of the Future; Proc. Int. Conf., Oliveira de Azeméis, Portugal*.
- Oliveira, V. & Pouzada, A. S. 2001. Desenvolvimento e Engenharia de Produto – Factor chave de competitividade. *O Molde* **50**: 6-10.
- Park, Y. & Colton, J. S. 2003. Sheet metal forming using polymer composite rapid prototype tooling. *Journal of Engineering Materials and Technology* **125**: 247-255.
- Pontes, A., Queirós, M., Martinho, P., Bártolo, P. & Pouzada, A. 2010. Experimental assessment of hybrid mould performance. *The International Journal of Advanced Manufacturing Technology* **50** (5): 441-448.
- Pontes, A. J., Queirós, M., Bártolo, P. J. & Pouzada, A. S. 2005. A Study on Design and Performance of Hybrid moulds for Injection Moulding. In *ICIT 2005 - 5th International Conference of Industrial Tools; Proc. Int. Conf., Bled, Slovenia, April*
- Pouzada, A. S. 2009. Hybrid moulds: a case of integration of alternative materials and rapid prototyping for tooling. *Virtual and Physical Prototyping* **4** (4): 195 - 202
- Tomori, T., Melkote, S. & Kotnis, M. 2004. Injection mold performance of machined ceramic filled epoxy tooling boards. *Journal of Materials Processing Technology* **145** (1): 126-133.
- Vasconcelos, P. V., Jorge Lino, F., Neto, R. J. & Paiva, R. 2006. Design Epoxy Resins Based Composites for Rapid Tooling Applications. In *5th Int. Conf. on Mechanics and Materials in Design; Proc. Int. Conf., Porto, Portugal, July 2006*.
- Wohlers, T. & Grimm, T. 2003. "Is CNC machining really better than RP?" *Moldmaking Technology*, Gardner Publications.