

# Fluorescence and two-photon absorption of push-pull aryl(bi)thiophenes: structure-property relationships

Emilie Genin,<sup>[a]</sup> Vincent Hugues,<sup>[a]</sup> Guillaume Clermont,<sup>[a]</sup> Cyril Herbivo,<sup>[b],[c]</sup> M. Cidália R. Castro,<sup>[b]</sup> Alain Comel,<sup>[c]</sup> M. Manuela M. Raposo<sup>[b]</sup> and Mireille Blanchard-Desce\*<sup>[a]</sup>

[a] Univ. Bordeaux, ISM, UMR 5255 CNRS, F-33400 Talence, France. Phone: +33 (5) 4000 6732; E-mail: [mireille.blanchard-desce@u-bordeaux1.fr](mailto:mireille.blanchard-desce@u-bordeaux1.fr)

[b] Center of Chemistry, University of Minho, Campus of Gualtar, 4710-057 Braga, Portugal. Phone: +351 253 604381

[c] Université de Lorraine, Institut Jean Barriol, Laboratoire de Chimie et Physique - Analyse Multi-échelles des Milieux Complexes, F-57048 Metz Cedex, France

## Abstract:

Photophysical and TPA properties of series of push-pull aryl(bi)thiophene chromophores bearing electron-donating (D) and electron-withdrawing (A) end-groups of increasing strength are presented. All compounds show an intense Intramolecular Charge Transfer (ICT) absorption band in the visible region. Increasing the D and/or A strength as well as the length of the conjugated path induces bathochromic and hyperchromic **shifts** of the absorption band as reported for analogous push-pull polyenes. Yet, in contrast with corresponding push-pull polyenes, a significant increase in fluorescence is observed. In particular, chromophores built from a phenyl-bithienyl conjugated path and bearing strong D and A end-groups were found to combine very large one and two-photon brightness as well as strong emission in the red/NIR region. These molecules hold promises as biphotonic fluorescent probes for bioimaging.

## 1. Introduction

Among the numerous classes of functional  $\pi$ -conjugated organic materials used as organic semiconductors, oligothiophenes have attracted widespread interest for many years<sup>1</sup> due to relation with their electronic/optical properties, high thermal and chemical stability and their relative ease of synthesis. They have been used for the fabrication of (opto)electronic devices such as organic field-effect transistors (OFETs),<sup>2</sup> organic light emitting diodes (OLEDs),<sup>3</sup> photovoltaic solar cells (OPVs and OSCs),<sup>2a, 4</sup> optically pumped lasers<sup>5</sup> and molecular

nanowires.<sup>6</sup> They have also been applied in applications such as non linear optics (NLO)<sup>7</sup> and biology.<sup>8</sup> In particular, the past decade has been marked by a growing interest in the design of NLO chromophores for two photon absorption (TPA) applications. These efforts have been driven by the many applications of TPA phenomenon in various fields including material science, biology and medicine.<sup>9</sup> Owing to the possibility it provides to use red-NIR excitation (allowing deeper penetration in scattering materials and tissues), and to the quadratic dependency of the TPA process on excitation intensity responsible for an intrinsic three-dimensional spatial resolution, technological applications have been developed such as Two-photon Excited Fluorescence (TPEF) laser-scanning microscopy,<sup>10, 11</sup> localised two-photon photodynamic therapy (TP-PDT),<sup>12</sup> localised photorelease of bioactive species,<sup>13</sup> 3D data storage,<sup>14</sup> optical power limiting,<sup>15</sup> and 3D microfabrication.<sup>9a, 15f, 16</sup> In particular, the increased popularity of TPEF microscopy for biology applications has motivated numerous efforts in the design of optimised fluorophores having large two-photon brightness (i.e.  $\sigma_2\Phi$  where  $\sigma_2$  is the TPA cross-section and  $\Phi$  the fluorescence quantum yield).<sup>9f, 11e-h, 15e, 17</sup> In addition, for easier detection in biological medium and tissues, red-emitting fluorophores are particularly helpful. In this context, we have been interested in investigating the potentialities of recently published push-pull oligothiophene derivatives whose second-order optical responses have been shown to be of interest.<sup>7c, 7f, 18</sup> Interestingly, (push-pull) oligothiophene derivatives have been largely described in the literature for organic solar cells purpose<sup>4a, 4d, 19</sup> but, to the best of our knowledge, only scarce examples of oligothiophene derivatives have been investigated for two-photon<sup>20</sup> or three-photon<sup>21</sup> excited photoluminescence up to now.

In this context, we herein report the detailed study of the fluorescence and TPA properties of series of push-pull aryl(bi)thiophene chromophores bearing various electron-donating (OR, NR<sub>2</sub>) groups and electron-withdrawing (formyl, dicyanovinyl and barbiturate) end-groups and either one or two thienyl units in the conjugated path. This allowed us to derive structure-property relationships aiming at optimisation of push-pull chromophores for TPEF microscopy.

## 2. Results and discussion

### 2.1 Compounds

All derivatives were easily obtained by Knoevenagel condensations starting from 2-formyl-5-arylthiophenes or 5-aryl-5'-formyl-2,2'-bithiophenes.<sup>7f, 18a</sup> As reported earlier, 2-formyl-5-arylthiophenes are easily obtained via Vilsmeier-Haack-Arnold reaction whereas formyl-

substituted 5-aryl-2,2'-bithiophenes are easily obtained via the Suzuki coupling of functionalised aryl boronic acids with 5'-bromo-5-formyl-2,2'-bithiophene.<sup>18a</sup>

In the present investigation, different formyl precursors **1a-d** and **3a, c-e** bearing different electron-donating end-groups (D) and having arylthiophene (**1**) or arylbithiophene (**3**)  $\pi$  conjugated linkers<sup>7f, 18a</sup> were selected in order to evaluate the influence of the electronic strength of the D substituents and of the length of the  $\pi$ -conjugated bridge on the fluorescence and TPA properties of these heteroaromatic aldehydes (Scheme 1). In order to increase the push-pull character of the derivatives, we also shifted to popular strong electron-withdrawing (A) end-groups such as dicyanovinyl (DCV) and 1,3-diethyl-2-thioxodihydropyrimidine-4,6-dione also known as 1,3-diethyl-2-thiobarbiturate (DETB). Such A end-groups have been shown to lead to very large optical non-linearities (both second- and third-order)<sup>7g, 22</sup> as well as long distance photo-induced charge transfer<sup>23</sup> in push-pull polyenes having dialkylamino donating end-groups. The dicyanovinyl derivatives **2** and **4** (already reported<sup>7f</sup>) and DETB derivatives (series **5** and **6**) were prepared in a similar way as related push-pull polyenes<sup>7g, 22</sup> by reacting aldehyde precursors **1** and **3** with malononitrile or 1,3-diethyl-2-thiobarbituric acid in refluxing ethanol, in the presence of a catalytic amount of piperidine (Scheme 1). New derivatives **5** and **6** were characterised by <sup>1</sup>H and <sup>13</sup>C NMR, IR, elemental analyses and HRMS.

## 2.2 Photophysical properties

The photophysical properties of derivatives **1-6** are collected in Table 1.

### *Absorption*

The absorption spectra in solution of all derivatives display an intense low-energy absorption band located in the near UV or visible region depending on the strength of the D and A end-groups as well as on the length on the conjugated path. This strong band, associated with high molar extinction coefficients (ranging from 2.2 to 6 10<sup>4</sup> mol<sup>-1</sup>.L.cm<sup>-1</sup>) can be ascribed to an intramolecular charge transfer (ICT) transition, as is the case for analogous related push-pull polyenes.<sup>7g, 22-23</sup> In the case of the red-shifted chromophores **4e**, **5a-d** and **6a-b, d, e** having the longer conjugated path and bearing the stronger D/A pairs, a second lower-intensity higher-energy absorption band located in the 350-450 nm range is also observed. This additional band can be ascribed to higher energy  $\pi$ - $\pi^*$  transition.

### *End-groups effect on ICT absorption band*

As previously observed for series **1-4**, comparison of the series of thiobarbituric acid derivatives **5** and **6** shows that increasing the electron-releasing strength of the D end-group (H →OMe→NEt<sub>2</sub>) induces a marked red-shift of the absorption band (Figure 1). Similarly increasing the electron-withdrawing strength of the A end-group (CHO→DCV→DET<sub>B</sub>) in series **1,2,5** leads to a significant bathochromic and hyperchromic shift as well as marked narrowing of the main absorption band (Figure 1). The same trend is also observed for the bithienyl series **3, 4** and **6**. The bathochromic and hyperchromic effects as well as the narrowing of the ICT band induced by increasing either D or A strength indicates that the polarisation increases in the ground state (corresponding to an increase of the contribution of the zwitterionic mesomeric form (Z) in the description of the electronic distribution) shifting the electronic structure towards a more “cyanine-like” distribution (scheme 1).<sup>24</sup> This behaviour is similar to that observed for related push-pull polyenes (i.e. having NR<sub>2</sub> donating end-groups and DCV or TET<sub>B</sub> acceptor end-groups).<sup>7g, 22</sup>

#### *Length and connector effect*

As expected, increasing the length of the  $\pi$ -conjugated bridge also has a marked influence on the photophysical properties. As an illustration, comparison of related derivatives **5** and **6** bearing strong DET<sub>B</sub> emphasises that increasing the number of thienyl moieties induces a marked bathochromic shift of the absorption band (Figure 2), as already reported for push-pull derivatives bearing formyl or DCV acceptors (series **1,3** and **2,4** respectively). This bathochromic shift is accompanied by a significant broadening in relation with a reduced contribution of the zwitterionic mesomeric form due to the higher cost of charge separation in bithienyl derivatives (Scheme 1). Such trend was also observed for related push-pull polyenes.<sup>7g, 22</sup> Furthermore, comparison of the absorption characteristics of push-pull (oligo)thienyl compounds **1d, 2d, 5d** bearing NMe<sub>2</sub> electron-releasing substituent and those of their polyenic analogues indicates that replacing two double bonds by one thienyl unit in the conjugated path leads to a clear blue-shift of the absorption maximum. Replacement of four double bonds by two thienyl units has a similar effect as indicated by comparison of absorption data of compounds **3e, 4e, 6d** and their polyenic analogues. This hypsochromic effect indicates a lower delocalisation in oligothienyl push-pull derivatives (i.e. lower contribution of the Z form as compared to analogous polyenes having the same number of double bonds in the conjugated path) in relation with the cost of charge separation associated with the loss of aromaticity of the thienyl units (scheme 1) . We observe that the largest

effects are obtained for derivatives having aldehydes and DETB (i.e. 1415 cm<sup>-1</sup> for compound **1d**, 1290 cm<sup>-1</sup> for compound **3e**, 1900 cm<sup>-1</sup> for compound **5d** and 1850 cm<sup>-1</sup> for compound **6d**).

### *Fluorescence*

Interestingly, in contrast to analogous push-pull polyenes,<sup>23b, 23d</sup> a number of derivatives from series **1-6,a-d** derivatives show significant fluorescence. This can be ascribed to the lower conformational stability of the (bi)thienyl  $\pi$ -linker as compared to polyenic chain, resulting in repression of efficient vibrational deactivation processes.

As observed from Table 1, the fluorescence characteristics are strongly dependent on the nature of the end-groups, as well as on the length of the conjugated path.

### *End-groups effect*

As was observed for absorption, increasing either the electron-releasing or electron-withdrawing character of the end-groups induces a marked bathochromic shift of the emission band (Figure 3), in agreement with the ICT nature of the transition. Moreover the fluorescence quantum yield tends to be higher for stronger donors. Only push-pull aldehydes **3** bent this rule since they display high fluorescence quantum yield values (up to 79%) regardless of the nature of the D end-group. As a result, all derivatives having strong D end-groups (i.e. **d,e** derivatives, D=NR<sub>2</sub>) show noticeable fluorescence, indicative of the  $\pi$ - $\pi^*$  nature of the lowest energy excited state due the ICT character of the transition which shifts its energy below that of the n- $\pi^*$  transition.

In contrast, considering both the thienyl **1, 2, 5** and bithienyl **3, 4, 6** series and comparing data for compounds having the same D substituent but different A end-groups (1→2→5 or 3→4→6), we observe that increasing the A strength (CHO→DCV→DETB) induces both a marked decrease of the Stokes Shift and a drastic decrease of the fluorescence quantum yields (Table 1). The decrease of the Stokes shift values parallels the narrowing of the ICT absorption band and emission and absorption red shifts and can be related to the shift of the electronic structure towards the cyanine limit. The steady decrease of the fluorescence quantum yield can be ascribed to combined effect of the reduction of the radiative decay rate (in connection with the red-shifted emission)<sup>25</sup> and increase of the non-radiative decay rates (see Table 1). In some cases (**2d, 4c, 5d, 6b**), the large non radiative decay rates suggest the

possible onset of competing processes occurring in the excited state such as photoinduced electron transfer.

### *Length effect*

Interestingly, the emission is significantly red-shifted when the conjugated path is lengthened (phenyl-thienyl  $\rightarrow$  phenyl-bithienyl) as illustrated in Figure 4 and indicated by comparison of corresponding chromophores of series **3,4,6** and **1,2,5**. This red-shift is even more pronounced that for absorption resulting in very large Stokes shift values (Table 1) and red or even NIR emission for bithienyl derivatives combining good donor (OR, NR<sub>2</sub>) and acceptor (DCV, DETB) end-groups. Even more strikingly, the increased length induces a marked fluorescence enhancement: whatever the series, bithienyl derivatives are found to be more fluorescent than their thienyl analogues (except for the case of compound **6d** whose low radiative decay rate is responsible for a slight loss of fluorescence). Hence, the bithienyl aldehyde **2a** displays an intense fluorescence (fluorescence quantum yield value of 35%) even in the absence of an electron-releasing *para*-substituent on the aromatic ring, thanks to the combined donor and transmitter nature of the thiophene moiety.

As a result of combined end-groups and length effects, push-pull derivatives built from the bithienyl  $\pi$ -connector and bearing good donor/acceptor end-groups (OMe, NR<sub>2</sub>/DCV, DETB: **4e**, **6b,d**) are found to be good red to NIR emitters.

## **2.3 Two-Photon Absorption**

Based on their fluorescence, we were able to determine the TPA characteristics of the derivatives **1b**, **1d**, **2b-d**, **3**, **4c**, **4e**, **5d** and **6d-e** by investigating their two-photon induced fluorescence in solution. TPA spectra were obtained in the 700-1200 nm spectral range through femtosecond two-photon excited fluorescence experiments and by following the methodology described by Webb and collaborators.<sup>26</sup> The corresponding data are gathered in Table 2. All compounds show a broad TPA band<sup>27</sup> (Figure 5) whose maximum is located at about twice the wavelength of the one-photon absorption (OPA) band, which indicates that the lowest excited state (ICT transition) is both one and two-photon allowed as expected for push-pull derivatives. In addition, fluorescent derivatives **4e** and **5-6d** having strong D and A groups show *an additional TPA band at higher energy* corresponding to the less intense absorption band located in the near UV (**4e**, **5d**) or violet (**6d**) region. Interestingly, whereas the ICT band is both one- and two-photon allowed, the second absorption band corresponding to a higher excited state is much more strongly two-photon allowed, leading to high TPA

cross-section values in a wide spectral range of interest for biological imaging (typically 1250 GM at 800 nm and 1570 GM at 1170 nm for the red-emitting compound **5d**). Such phenomenon has already been observed in octupolar merocyanines.<sup>28</sup>

#### *End-groups effect*

For the different series, comparisons of chromophores bearing different electron-releasing groups showed that increasing the donor strength leads both to a bathochromic shift of the TPA band (in connection with the ICT band red-shift) and a marked enhancement of the maximum TPA cross section ( $\sigma_2$ ) values (Table 2) as illustrated in Figure 5. A similar trend is obtained when increasing the acceptor strength (Figure 5). Interestingly, this hyperchromic effect is much more pronounced for TPA than OPA in relation with the pronounced ICT character of the transition.<sup>24b</sup>

#### *Length effect*

Finally the nature of the  $\pi$ -conjugated bridge strongly influences the TPA properties of the compounds. Increasing the number of thiophene moieties also induces a red-shift of the TPA (paralleling the red-shift of the ICT absorption band) and leads to a marked enhancement of the TPA cross-section values ( $\sigma_2$ ) as illustrated Figure 6. As a result, push-pull derivatives having two thienyl units and combining strong D and A end-groups (typically D=NR<sub>2</sub> and A=DCV or DETB) were found to show very large maximum TPA cross-section in the spectral region of interest for bioimaging (1600 GM at 1200 nm for NIR emitting compound **6d**).

### **3. Experimental section**

#### **3.1 Compounds**

The synthesis and characterisation of compounds **1-4,a-e** have been described earlier.<sup>7f, 18a</sup> New compounds **5-6,a-e** have been synthesised following the same procedure.

Thin layer chromatography was carried out on 0.25 mm thick precoated silica plates (Merck FertigplattenKieselgel 60F<sub>254</sub>). Melting points were measured on a Gallenkamp melting point apparatus. NMR spectra were obtained on a Varian Unity Plus Spectrometer at an operating frequency of 300 MHz for <sup>1</sup>H NMR and 75.4 MHz for <sup>13</sup>C NMR or a Bruker Avance III 400 at an operating frequency of 400 MHz for <sup>1</sup>H NMR and 100.6 MHz for <sup>13</sup>C NMR using the solvent peak as internal reference at 25 °C. All chemical shifts are given in ppm using

$\delta_{\text{HMe}_4\text{Si}} = 0$  ppm as reference and  $J$  values are given in Hz. Assignments were made by comparison of chemical shifts, peak multiplicities and  $J$  values and were supported by spin decoupling-double resonance and bidimensional heteronuclear HMBC and HMQC correlation techniques. IR spectra were run on a FTIR Perkin-Elmer 1600 spectrophotometer in nujol or in KBr. Elemental analyses were carried out on a Leco CHNS 932 instrument. Low and high resolution mass spectrometry analyses were performed at the "C.A.C.T.I. - Unidad de Espectrometria de Masas", at University of Vigo, Spain. 1,3-Diethyl-2-thiobarbituric acid was purchased from Sigma-Aldrich and used without further purification.

**General procedure for the synthesis of arylthiophene and arylbithiophenethiobarbituric acid derivatives 5-6 from the corresponding formyl precursors 1 and 3 by Knoevenagel condensation**

To a solution of 1,3-diethyl-2-thiobarbituric acid (80 mg, 0.38 mmol, 1.2 equiv) and aldehydes **1** or **3** (0.32 mmol, 1.0 equiv) in ethanol (20 ml) was added piperidine (1 drop). The solution was stirred at reflux during different reaction times (3-4 h) and cooled until room temperature. The mixture was filtered and the crude solid was washed with diethyl ether. Recrystallisation from dichloromethane/petroleum ether gave the pure compounds.

**1,3-diethyl-dihydro-5-((5'-phenylthiophen-2'-yl)methylene)- 2-thioxopyrimidine-4,6(1H,5H)-dione 5a**

Orange solid (51%). Mp 223-224 °C. IR(KBr)  $\nu$  3088, 1657, 1547, 1506, 1394, 1331  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR (DMSO- $d_6$ )  $\delta$  1.20 (m, 6 H, 2 x  $\text{NCH}_2\text{CH}_3$ ), 4.44 (m, 4 H, 2x $\text{NCH}_2\text{CH}_3$ ), 7.50 (m, 3 H, 3''-H, 4''-H and 5''-H), 7.90 (m, 3 H, 2''-H, 6''-H and 4'-H), 8.31 (d, 1 H,  $J=4.2$  Hz, 3'-H), 8.66 (s, 1H, =CH).  $^{13}\text{C}$  RMN ( $\text{CDCl}_3$ )  $\delta$ : 12.4, 12.5, 43.2, 44.0, 110.4, 124.8, 126.8, 129.2, 130.0, 136.8, 147.2, 149.8, 152.1, 159.8, 161.0, 161.4, 178.7. Anal. Calcd. for  $\text{C}_{19}\text{H}_{18}\text{N}_2\text{O}_2\text{S}_2$ : C, 61.60; H, 4.90; N, 7.56; S, 17.3. Found: C, 61.70; H, 5.04; N, 7.58; S, 16.9.

**1,3-diethyl-5-((5'-(4''-methoxyphenylthiophen-2'-yl)-methylene)-2-thioxodihydropyrimidine-4,6(1H,5H)-dione 5b**

Red solid (73%). Mp 221-223 °C. IR(KBr)  $\nu$  3089, 2948, 1656, 1603, 1493, 1395, 1333, 1257, 1031  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR (DMSO- $d_6$ )  $\delta$  1.20 (m, 6 H, 2x $\text{NCH}_2\text{CH}_3$ ), 3.83 (s, 3 H,  $\text{OCH}_3$ ), 4.44 (m, 4 H, 2x $\text{NCH}_2\text{CH}_3$ ), 7.06 (d, 2 H,  $J=8.9$  Hz, 3''-H and 5''-H), 7.79 (d, 1 H,  $J=4.2$  Hz, 4'-H), 7.86 (d, 2 H,  $J=8.9$  Hz, 2''-H and 6''-H), 8.28 (d, 1 H,  $J=4.2$  Hz, 3'-H), 8.64 (s, 1 H,



C=CH).  $^{13}\text{C}$  RMN (DMSO- $d_6$ )  $\delta$  12.4, 12.5, 43.1, 43.9, 55.5, 109.5, 114.7, 123.9, 125.8, 128.4, 135.9, 147.7, 149.7, 159.9, 161.1, 161.4, 162.1, 178.7. Anal. Calcd. for  $\text{C}_{20}\text{H}_{20}\text{N}_2\text{O}_3\text{S}_3$ : C, 59.98; H, 5.03; N, 6.99; S, 16.0. Found: C, 59.75; H, 5.08; N, 7.00; S, 15.7.

**1,3-diethyl-5-((5'-(4''-ethoxyphenylthiophen-2'-yl)-methylene)-2-thioxodihydropyrimidine-4,6(1H,5H)-dione 5c**

Violet solid (58 %). Mp 198-199 °C. IR(KBr)  $\nu$ 3081, 2934, 1651, 1603, 1486, 1388, 1331, 1255, 1052  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR (DMSO- $d_6$ )  $\delta$  1.20 (m, 6 H, 2 x  $\text{NCH}_2\text{CH}_3$ ), 1.35 (t, 3 H,  $\text{J}=6.9$  Hz,  $\text{OCH}_2\text{CH}_3$ ), 4.10 (q, 2 H,  $\text{J}=6.9$  Hz,  $\text{OCH}_2\text{CH}_3$ ), 4.44 (m, 4 H, 2 x  $\text{NCH}_2\text{CH}_3$ ), 7.05 (d, 2 H,  $\text{J}=8.6$  Hz, 3''-H and 5''-H), 7.79 (d, 1H,  $\text{J}=4.3$  Hz, 4'-H), 7.86 (d, 2 H,  $\text{J}=8.6$  Hz, 2''-H and 6''-H), 8.29 (d, 1H,  $\text{J}=4.3$  Hz, 3'-H), 8.64 (s, 1 H, C=CH).  $^{13}\text{C}$  RMN (DMSO- $d_6$ )  $\delta$  12.5, 14.7, 43.1, 43.9, 63.7, 109.4, 115.1, 123.9, 125.6, 128.4, 135.9, 147.8, 149.7, 159.9, 160.8, 161.1, 162.3, 178.7. MS (microTOF)  $m/z$  (%): 415 ( $\text{M}^+$ , 100), 338 (36). HRMS :  $m/z$  (microTOF) for  $\text{C}_{21}\text{H}_{23}\text{N}_2\text{O}_3\text{S}_2$ ; calcd 415.1145 found: 415.1127. Anal. Calcd. for  $\text{C}_{21}\text{H}_{22}\text{N}_2\text{O}_3\text{S}_3$ : C, 60.84; H, 5.35; N, 6.76; S, 15.5. Found: C, 60.91; H, 5.30; N, 6.76; S, 15.3.

**1,3-diethyl-5-((5'-(4''-N,N-dimethylaminophenylthiophen-2'-yl)-methylene)-2-thioxodihydropyrimidine-4,6(1H,5H)-dione 5d**

Violet solid (81%). Mp 260-262 °C. IR(KBr) 3073, 2931, 1649, 1604, 1488, 1387, 1362, 1329  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR ( $\text{CDCl}_3$ )  $\delta$  1.35 (m, 6 H, 2x $\text{NCH}_2\text{CH}_3$ ), 3.11 (s, 6 H,  $\text{N}(\text{CH}_3)_2$ ), 4.60 (m, 4 H, 2x $\text{NCH}_2\text{CH}_3$ ), 6.70 (d, 2 H,  $\text{J}=9.1$  Hz, 3''-H and 5''-H), 7.40 (d, H,  $\text{J}=4.3$  Hz, 4'-H), 7.70 (d, 2 H,  $\text{J}=9.1$  Hz, 2''-H and 6''-H), 7.82 (d, 1H,  $\text{J}=4.3$  Hz, 3'-H), 8.59 (s, 1 H, C=CH).  $^{13}\text{C}$  RMN ( $\text{CDCl}_3$ )  $\delta$  12.4, 12.5, 40.1, 43.0, 43.8, 107.9, 112.0, 120.7, 122.8, 128.3, 134.8, 148.5, 149.2, 151.8, 160.0, 161.4, 164.6, 178.7. Anal. Calcd. for  $\text{C}_{21}\text{H}_{23}\text{N}_3\text{O}_2\text{S}_2$ : C, 60.99; H, 5.61; N, 10.2; S, 15.5. Found: C, 60.97; H, 5.68; N, 10.1; S, 15.2.

**1,3-diethyl-dihydro-5-((5-(5-phenylthiophen-2-yl)thiophen-2-yl)methylene)-2-thioxopyrimidine-4,6(1H,5H)-dione 6a.**

Pink solid (60%). Mp 240-241 °C. IR(nujol)  $\nu$  1685, 1655, 1548, 1528, 1495, 1414, 1328, 1301, 1266, 1171, 1152, 1105, 1073, 998, 972, 897, 806, 782, 759, 722, 759, 722, 691, 640, 608  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR (DMSO- $d_6$ )  $\delta$  1.22 (m, 6 H, 2x $\text{NCH}_2\text{CH}_3$ ), 4.42 (m, 4 H, 2x $\text{NCH}_2\text{CH}_3$ ), 7.43 (m, 3 H, 3''-H, 4''-H and 5''-H), 7.66 (d, 1 H,  $\text{J}=3.9$  Hz, 4'-H), 7.77 (m, 3 H, 3'-H, 2''-H and 6''-H), 7.81 (d, 1H,  $\text{J}=3.9$  Hz, 3-H), 8.28 (d, 1H,  $\text{J}=3.9$  Hz, 4-H), 8.64 (s, 1H, =CH). MS

(microTOF)  $m/z$  (%): 453 ( $M^+ + 1$ , 20), 452 ( $M^+$ , 5), 338 (68), 316 (17), 288 (44), 239 (14), 197 (90), 175 (9). HRMS:  $m/z$  (microTOF) for  $C_{23}H_{21}N_2O_2S_3$ ; calcd 453.07204; found: 453.07597. Anal. Calcd. for  $C_{23}H_{20}N_2O_2S_3$ : C, 61.03; H, 4.45; N, 6.19; S, 21.2. Found: C, 60.78; H, 4.23; N, 6.15; S, 21.3.

**5-((5-(5-(4-(Methoxy)phenyl)thiophen-2-yl)thiophen-2-yl)methylene)-1,3-diethyl-dihydro-2-thioxopyrimidine-4,6(1H,5H)-dione 6b.**

Dark blue solid (85%). Mp 263-265 °C. IR(nujol)  $\nu$  1685, 1650, 1556, 1531, 1505, 1486, 1170, 1153, 1105, 1026, 974, 897, 824, 815, 803, 794, 783, 751, 722, 668, 648, 632, 582, 550  $cm^{-1}$ .  $^1H$  NMR (DMSO- $d_6$ )  $\delta$  1.22 (m, 6 H,  $2 \times NCH_2CH_3$ ), 3.80 (s, 3 H, OCH<sub>3</sub>), 4.45 (m, 4 H,  $2 \times NCH_2CH_3$ ), 7.00 (d, 2 H,  $J=8.7$  Hz, 3''-H and 5''-H), 7.55 (d, 1 H,  $J=3.9$  Hz, 4'-H), 7.72 (m, 3 H, 2''-H and 6''-H and 3'-H), 7.78 (d, 1H,  $J=3.9$  Hz, 3-H), 8.27 (d, 1H,  $J=3.9$ Hz, 4-H), 8.64 (s, 1H, =CH). MS (EI)  $m/z$  (%): 482 ( $M^+$ , 100), 449 (38), 422 (10), 394 (29), 366 (5), 353 (8), 326 (45), 298 (9), 281 (45), 272 (29), 253 (38), 229 (12), 200 (18), 171 (8), 148 (4). HRMS:  $m/z$  (EI) for  $C_{24}H_{22}N_2O_3S_3$ ; calcd 482.0800; found: 482.0793.

**5-((5-(5-(4-(Dimethylamino)phenyl)thiophen-2-yl)thiophen-2-yl)methylene)-1,3-diethyl-dihydro-2-thioxopyrimidine-4,6(1H,5H)-dione 6d.**

Green solid (89%). Mp 246-248 °C. IR(nujol)  $\nu$  1682, 1656, 1539, 1513, 1330, 1301, 1258, 1213, 1193, 1151, 1103, 1075, 1059, 1000, 985, 959, 912, 897, 817, 796, 782, 755, 741, 720, 682, 663, 652, 628, 608, 584, 551  $cm^{-1}$ .  $^1H$  NMR (DMSO- $d_6$ )  $\delta$  1.22 (m, 6 H,  $2 \times NCH_2CH_3$ ), 2.96 (s, 6H,  $N(CH_3)_2$ ), 4.45 (m, 4 H,  $2 \times NCH_2CH_3$ ), 6.75 (d, 2 H,  $J=8.7$  Hz, 3''-H and 5''-H), 7.44 (d, 1 H,  $J=3.9$  Hz, 4'-H), 7.58 (d, 2 H,  $J=8.7$  Hz, 2''-H and 6''-H), 7.68 (d, 1 H,  $J=4.2$  Hz, 3-H), 7.77 (d, 1 H,  $J=3.9$  Hz, 3'-H), 8.25 (d, 1 H,  $J=4.2$  Hz, 4-H), 8.62 (s, 1H, =CH). MS (microTOF)  $m/z$  (%): 496 ( $M^+ + 1$ , 45), 495 ( $M^+$ , 20), 413 (17), 379 (13), 299 (91), 226 (5). HRMS:  $m/z$  (microTOF) for  $C_{25}H_{25}N_3O_2S_3$ ; calcd 495.1109; found: 495.1103. Anal. Calcd. for  $C_{25}H_{25}N_3O_2S_3$ : C, 60.58; H, 5.08; N, 8.48; S, 19.4. Found: C, 60.63; H, 5.08; N, 8.58; S, 18.9.

**5-((5-(5-(4-(Diethylamino)phenyl)thiophen-2-yl)thiophen-2-yl)methylene)-1,3-diethyl-dihydro-2-thioxopyrimidine-4,6(1H,5H)-dione 6e.**

Green solid (96%). Mp 199-201 °C. IR(nujol)  $\nu$  1684, 1655, 1605, 1551, 1539, 1516, 1481, 1411, 1395, 1356, 1307, 1269, 1250, 1231, 1217, 1159, 1108, 1096, 1077, 1054, 1019, 1001,

956, 925, 900, 881, 861, 813, 793, 779, 740, 735, 720, 680, 651, 625, 610, 584, 547  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR (DMSO- $d_6$ )  $\delta$  1.10 (t, 6 H,  $J=6.9$  Hz,  $\text{Ph-N}(\text{CH}_2\text{CH}_3)_2$ ), 1.22 (m, 6 H,  $2\times\text{NCH}_2\text{CH}_3$ ), 3.38 (q, 4 H,  $J=6.9$  Hz,  $\text{PhN}(\text{CH}_2\text{CH}_3)_2$ ), 4.44 (m, 4 H,  $2\times\text{NCH}_2\text{CH}_3$ ), 6.71 (d, 2H,  $J=8.7$  Hz, 3''-H and 5''-H), 7.40 (d, 2 H,  $J=3.9$  Hz, 4'-H), 7.54 (d, 2 H,  $J=8.7$  Hz, 2''-H and 6''-H), 7.68 (d, 1 H,  $J=3.9$  Hz, 3'-H), 7.76 (d, 1 H,  $J=3.9$  Hz, 3-H), 8.25 (d, 1 H,  $J=3.9$  Hz, 4-H), 8.61 (s, 1H, =CH). MS (microTOF)  $m/z$  (%): 524 ( $\text{M}^++1$ , 91), 523 ( $\text{M}^+$ , 31), 497 (24), 453 (30), 393 (32), 349 (27), 318 (16). HRMS:  $m/z$  (microTOF) for  $\text{C}_{27}\text{H}_{30}\text{N}_3\text{O}_2\text{S}_3$ ; calcd 524.1455; found: 524.1495. Anal. Calcd. for  $\text{C}_{27}\text{H}_{29}\text{N}_3\text{O}_2\text{S}_3$ : C, 61.92; H, 5.58; N, 8.02; S, 18.4. Found: C, 61.62; H, 5.31; N, 7.99; S, 18.3.

### 3.2 Photophysical study

All photophysical studies have been performed with freshly-prepared air-equilibrated solutions at room temperature (298 K). UV/Vis absorption spectra of  $10^{-5}$  M chloroform solutions were recorded on a Jasco V-570 spectrophotometer. Steady-state and time-resolved fluorescence measurements were performed on dilute solutions (*ca.*  $10^{-6}$  M, optical density < 0.1) contained in standard 1 cm quartz cuvettes using an Edinburgh Instruments (FLS920) spectrometer in photon-counting mode. Emission spectra were obtained, for each compound, under excitation at the wavelength of the absorption maximum. Fluorescence quantum yields were measured according to literature procedures. Cresyl violet or Quinine bisulfate in 1N  $\text{H}_2\text{SO}_4$  were used as standards depending on the emission spectral range.<sup>29</sup>

The lifetime values were obtained from the reconvolution fit analysis (Edinburgh F900 analysis software) of decay profiles obtained using the FLS920 instrument under excitation with a nitrogen-filled nanosecond flashlamp. The quality of the fits was evidenced by the reduced  $\chi^2$  value ( $\chi^2 < 1.1$ ).

### 3.4 Two-photon absorption

TPA cross sections ( $\sigma_2$ ) were determined from the two-photon excited fluorescence (TPEF) cross sections ( $\sigma_2\Phi$ ) and the fluorescence emission quantum yield ( $\Phi$ ). TPEF cross sections of  $10^{-4}$  M chloroform solutions were measured relative to fluorescein in 0.01M aqueous NaOH for 715-980 nm,<sup>26</sup> using the well-established method described by Xu and Webb<sup>26a</sup> and the appropriate solvent-related refractive index corrections.<sup>30</sup> Reference values between 700 and 715 nm for fluorescein were taken from literature.<sup>31</sup> The quadratic dependence of the fluorescence intensity on the excitation power was checked for each sample and all

wavelengths, indicating that the measurements were carried out in intensity regimes where saturation or photodegradation did not occur.

Measurements were conducted using excitation sources delivering fs pulses. This is preferred in order to avoid excited state absorption during the pulse duration, a phenomenon which has been shown to lead to overestimated TPA cross-section values. To span the 700-980 nm range, a Nd:YLF-pumped Ti:sapphire oscillator was used generating 150 fs pulses at a 76 MHz rate. To span the 1000-1400 nm range, an OPO (PP-BBO) was added to the setup to collect and modulate the output signal of the Ti:sapphire oscillator. The excitation was focused into the cuvette through a microscope objective (10X, NA 0.25). The fluorescence was detected in epifluorescence mode via a dichroic mirror (Chroma 675dcxru) and a barrier filter (Chroma e650sp-2p) by a compact CCD spectrometer module BWTek BTC112E. Total fluorescence intensities were obtained by integrating the corrected emission.

#### 4. Conclusion

The investigation of the photophysical and two-photon absorption properties in a set of series of push-pull derivatives having one or two thienyl moieties in the  $\pi$ -conjugated system allowed us to derive helpful structure-properties relationships. These compounds show intense absorption in the near UV-visible region, as well as two-photon absorption in the NIR region in connection with a low-lying intramolecular charge transfer excited state. Interestingly, in such compounds, increasing the length of the conjugated system as well as the strength of the D end-groups allows to *increase* and bathochromically shift both one-photon and two-photon absorption as well as fluorescence. As a result, orange to red bright emitting fluorophores were obtained as illustrated for example in the cases of compounds **3e** ( $\lambda_{em} = 612$  nm and  $\Phi = 74\%$ ) and **4e** ( $\lambda_{em} = 727$  nm and  $\Phi = 34\%$ ) that combine strong  $NEt_2$  donor end-groups and phenyl-bi(thienyl) conjugated path. In contrast, increasing the strength of the A end-groups also leads to a significant bathochromic shift of both one- and two-photon absorption and emission as well as an increase of (one and two-photon) absorption (ICT) bands but at the cost of a reduction of the fluorescence quantum yield. As a result when combining strong D and A end-groups, fluorophores emitting in the NIR region, were obtained as illustrated in the case of fluorophore **6d** ( $\lambda_{em} = 781$  nm and  $\Phi = 6\%$ ).

All push-pull derivatives show a broad TPA band located in the NIR region whose position matches well the intense one-photon absorption band located in the visible, indicating that the ICT transition is both one and two-photon allowed. This TPA band is significantly

red-shifted and its magnitude is found to increase considerably with both the strength of the end-groups and the length of the conjugated path. Such enhancement has also been observed in different quadrupolar and octupolar derivatives with different  $\pi$ -connectors (i.e. vinylene-arylene).<sup>11e, 17d-g</sup> As a result, push-pull derivatives **4e**, **5d** and **6d** which bear strong D (i.e. NR<sub>2</sub>) and A (DCV or DETB) end-groups were found to combine large TPA cross-section in the 1000-1200 nm spectral range (up to 1600 GM), as well as red or NIR emission. These spectral characteristics are of major interest for biological microscopic imaging due to the reduced scattering they provide in tissues. The push-pull arylbithiophenes combining strong D and A end-groups thus hold promise for the design of biphotonic fluorescent probes for bioimaging. We are currently investigating this route.

## 5. Acknowledgements

MBD gratefully thanks the Conseil Regional d'Aquitaine for financial support (Chaire d'Accueil grant). We also acknowledge Bordeaux 1 University and CNRS for financial support. The spectrophotometer, spectrofluorimeter and OPO were purchased thanks to ATIP and CNRS equipment grants. EG and GC thanks CNRS for a research fellowship (Délégation) and NOEMI respectively.

MMMR thanks the Fundação para a Ciência e Tecnologia (Portugal) and FEDER-COMPETE for financial support through the Centro de Química - Universidade do Minho, through project PTDC/QUI/66251/2006 (FCOMP-01-0124-FEDER-007429). The NMR spectrometer Bruker Avance III 400 is part of the National NMR Network and was purchased within the framework of the National Program for Scientific Re-equipment, contract REDE/1517/RMN/2005 with funds from POCI 2010 (FEDER) and FCT.

## References

1. a) J. Roncali, Synthetic principles for bandgap control in linear pi-conjugated systems, *Chem. Rev.*, 1997, **97**, 173-205; b) A. Mishra, C.-Q. Ma and P. Baeuerle, Functional Oligothiophenes: Molecular Design for Multidimensional Nanoarchitectures and Their Applications, *Chem. Rev.*, 2009, **109**, 1141-1276; c) *Handbook of Thiophene-Based Materials: Applications in Organic electronics and Photonics* (Eds: F. Perepichka, D.F. Perepichka), Wiley, New York, **2009**; d) G. Barbarella, M. Melucci and G. Sotgiu, The versatile thiophene: An overview of recent research on thiophene-based materials, *Adv. Mater.*, 2005, **17**, 1581-1593; e) A. Pron, P. Gawrys, M. Zagorska, D. Djurado and R. Demadrille, Electroactive materials for organic electronics: preparation strategies, structural aspects and characterization techniques, *Chem. Soc. Rev.*, 2010, **39**, 2577-2632.

2. a) P. M. Beaujuge and J. M. J. Fréchet, Molecular Design and Ordering Effects in  $\pi$ -Functional Materials for Transistor and Solar Cell Applications, *J. Am. Chem. Soc.*, 2011, **133**, 20009-20029; b) A. R. Murphy and J. M. J. Fréchet, Organic Semiconducting Oligomers for Use in Thin Film Transistors, *Chem. Rev.*, 2007, **107**, 1066-1096; c) C. Wang, H. Dong, W. Hu, Y. Liu and D. Zhu, Semiconducting  $\pi$ -Conjugated Systems in Field-Effect Transistors: A Material Odyssey of Organic Electronics, *Chem. Rev.*, 2011, **112**, 2208-2267.
3. a) J. Roncali, Linear  $\pi$ -conjugated systems derivatized with C-60-fullerene as molecular heterojunctions for organic photovoltaics, *Chem. Soc. Rev.*, 2005, **34**, 483-495; b) J. Pina, S. S. de Melo, H. D. Burrows, R. M. F. Batista, S. P. G. Costa and M. M. Raposo, Spectral and photophysical characterization of donor- $\pi$ -acceptor arylthienyl- and bithienyl-benzothiazole derivatives in solution and solid state, *J. Phys. Chem. A*, 2007, **111**, 8574-8578; c) R. M. F. Batista, S. P. G. Costa, M. Belsley and M. M. M. Raposo, Synthesis and optical properties of novel, thermally stable phenanthrolines bearing an arylthienyl-imidazo conjugation pathway, *Dyes Pigments*, 2009, **80**, 329-336; d) F. Mariano, M. Mazzeo, Y. Duan, G. Barbarella, L. Favaretto, S. Carallo, R. Cingolani and G. Gigli, Very low voltage and stable p-i-n organic light-emitting diodes using a linear S,S-dioxide oligothiophene as emitting layer, *Appl. Phys. Lett.*, 2009, **94**, 063510; e) X. H. Zhu, J. B. Peng, Y. Cao and J. Roncali, Solution-processable single-material molecular emitters for organic light-emitting devices, *Chem. Soc. Rev.*, 2011, **40**, 3509-3524.
4. a) F. Zhang, D. Wu, Y. Xu and X. Feng, Thiophene-based conjugated oligomers for organic solar cells, *J. Mater. Chem.*, 2011, **21**, 17590-17600; b) A. Mishra and P. Bäuerle, Small Molecule Organic Semiconductors on the Move: Promises for Future Solar Energy Technology, *Angew. Chem. Int. Ed.*, 2012, **51**, 2020-2067; c) S. Ko, E. Verploegen, S. Hong, R. Mondal, E. T. Hoke, M. F. Toney, M. D. McGehee and Z. Bao, 3,4-Disubstituted Polyalkylthiophenes for High-Performance Thin-Film Transistors and Photovoltaics, *J. Am. Chem. Soc.*, 2011, **133**, 16722-16725; d) C. Mallet, G. Savitha, M. Allain, V. Kozmik, J. Svoboda, P. Frere and J. Roncali, Synthesis and Electronic Properties of D-A-D Triads Based on 3-Alkoxy-4-cyanothiophene and Benzothienothiophene Blocks, *J. Org. Chem.*, 2012, **77**, 2041-2046; e) Y.-J. Cheng, S.-H. Yang and C.-S. Hsu, Synthesis of Conjugated Polymers for Organic Solar Cell Applications, *Chem. Rev.*, 2009, **109**, 5868-5923; f) R. Schueppel, K. Schmidt, C. Uhrich, K. Schulze, D. Wynands, J. L. Bredas, E. Brier, E. Reinold, H. B. Bu, P. Baeuerle, B. Maennig, M. Pfeiffer and K. Leo, Optimizing organic photovoltaics using tailored heterojunctions: A photoinduced absorption study of oligothiophenes with low band gaps, *Phys. Rev. B*, 2008, **77**, 085311.
5. I. D. W. Samuel and G. A. Turnbull, Organic semiconductor lasers, *Chem. Rev.*, 2007, **107**, 1272-1295.
6. J.-i. Nishida, T. Miyagawa and Y. Yamashita, Novel Thiophene Oligomers Containing a Redox Active Hexaarylethane Unit, *Org. Lett.*, 2004, **6**, 2523-2526.
7. a) S. R. Marder, C. B. Gorman, B. G. Tiemann and L. T. Cheng, Stronger acceptors can diminish nonlinear optical-response in simple donor-acceptor polyenes, *J. Am. Chem. Soc.*, 1993, **115**, 3006-3007; b) S. R. Marder, L. T. Cheng, B. G. Tiemann, A. C. Friedli, M. Blanchard-Desce, J. W. Perry and J. Skindhoj, Large 1st hyperpolarizabilities in push-pull polyenes by tuning of the bond-length alternation and aromaticity, *Science*, 1994, **263**, 511-514; c) S. P. G. Costa, R. M. F. Batista, P. Cardoso, M. Belsley and M. M. M. Raposo, 2-arylthienyl-substituted 1,3-benzothiazoles as new nonlinear optical chromophores, *Eur. J. Org. Chem.*, 2006, 3938-3946; d) R. M. F. Batista, S. P. G. Costa, M. Belsley, C. Lodeiro and M. M. M.

- Raposo, Synthesis and characterization of novel (oligo)thienyl-imidazophenanthrolines as versatile pi-conjugated systems for several optical applications, *Tetrahedron*, 2008, **64**, 9230-9238; e) M. M. M. Raposo, A. Ferreira, M. Belsley and J. Moura, 5'-alkoxy-2,2'-bithiophene azo dyes: a novel promising series of NLO-chromophores, *Tetrahedron*, 2008, **64**, 5878-5884; f) C. Herbivo, A. Comel, G. Kirsch, A. M. C. Fonseca, M. Belsley and M. M. M. Raposo, Synthesis and characterization of novel, thermally stable 2-aryl-5-dicyanovinylthiophenes and 5-aryl-5'-dicyanovinyl-2,2'-bithiophenes as potentially promising non-linear optical materials, *Dyes Pigments*, 2010, **86**, 217-226; g) M. Blanchard-Desce, V. Alain, P. V. Bedworth, S. R. Marder, A. Fort, C. Runser, M. Barzoukas, S. Lebus and R. Wortmann, Large Quadratic Hyperpolarizabilities with Donor-Acceptor Polyenes Exhibiting Optimum Bond Length Alternation: Correlation Between Structure and Hyperpolarizability, *Chem. Eur. J.*, 1997, **3**, 1091-1104.
8. a) G. Ridolfi, N. Camaioni, P. Samori, M. Gazzano, G. Accorsi, N. Armaroli, L. Favaretto and G. Barbarella, All-thiophene donor-acceptor blends: photophysics, morphology and photoresponse, *J. Mater. Chem.*, 2005, **15**, 895-901; b) I. Palama, F. Di Maria, I. Viola, E. Fabiano, G. Gigli, C. Bettini and G. Barbarella, Live-Cell-Permeant Thiophene Fluorophores and Cell-Mediated Formation of Fluorescent Fibrils, *J. Am. Chem. Soc.*, 2011, **133**, 17777-17785; c) M. L. Capobianco, G. Barbarella and A. Manetto, Oligothiophenes as Fluorescent Markers for Biological Applications, *Molecules*, 2012, **17**, 910-933; d) M. Duca, B. Dozza, E. Lucarelli, S. Santi, A. Di Giorgio and G. Barbarella, Fluorescent labeling of human mesenchymal stem cells by thiophene fluorophores conjugated to a lipophilic carrier, *Chem. Commun.*, 2010, **46**, 7948-7950; e) G. Sotgiu, M. Zambianchi, G. Barbarella, F. Aruffo, F. Cipriani and A. Ventola, Rigid-Core Fluorescent Oligothiophene-S,S-dioxide Isothiocyanates. Synthesis, Optical Characterization, and Conjugation to Monoclonal Antibodies, *J. Org. Chem.*, 2003, **68**, 1512-1520; f) G. Barbarella, M. Zambianchi, O. Pudova, V. Paladini, A. Ventola, F. Cipriani, G. Gigli, R. Cingolani and G. Citro, Oligothiophene Isothiocyanates as a New Class of Fluorescent Markers for Biopolymers, *J. Am. Chem. Soc.*, 2001, **123**, 11600-11607.
9. a) M. Pawlicki, H. A. Collins, R. G. Denning and H. L. Anderson, Two-Photon Absorption and the Design of Two-Photon Dyes, *Angew. Chem. Int. Ed.*, 2009, **48**, 3244-3266; b) F. Terenziani, C. Katan, E. Badaeva, S. Tretiak and M. Blanchard-Desce, Enhanced Two-Photon Absorption of Organic Chromophores: Theoretical and Experimental Assessments, *Adv. Mater.*, 2008, **20**, 4641-4678; c) G. S. He, L.-S. Tan, Q. Zheng and P. N. Prasad, Multiphoton Absorbing Materials: Molecular Designs, Characterizations, and Applications, *Chem. Rev.*, 2008, **108**, 1245-1330; d) H. M. Kim and B. R. Cho, Two-Photon Probes for Intracellular Free Metal Ions, Acidic Vesicles, And Lipid Rafts in Live Tissues, *Acc. Chem. Res.*, 2009, **42**, 863-872; e) H. Myung Kim and B. Rae Cho, Two-photon materials with large two-photon cross sections. Structure-property relationship, *Chem. Commun.*, 2009, 153-164; f) M. Blanchard-Desce, Molecular engineering of NLO-phores for new NLO microscopies, *C. R. Physique*, 2002, **3**, 439-448; g) M. Drobizhev, N. S. Makarov, S. E. Tillo, T. E. Hughes and A. Rebane, Describing Two-Photon Absorptivity of Fluorescent Proteins with a New Vibronic Coupling Mechanism, *J. Phys. Chem. B*, 2012, **116**, 1736-1744; h) M. Drobizhev, N. S. Makarov, S. E. Tillo, T. E. Hughes and A. Rebane, Two-photon absorption properties of fluorescent proteins, *Nat. Methods*, 2011, **8**, 393-399.
10. a) W. Denk, J. H. Strickler and W. W. Webb, Two-photon laser scanning fluorescence microscopy, *Science*, 1990, **248**, 73-76; b) K. Svoboda, W. Denk, D. Kleinfeld and D.

- W. Tank, In vivo dendritic calcium dynamics in neocortical pyramidal neurons, *Nature*, 1997, **385**, 161-165.
11. a) H. Meier, Conjugated Oligomers with Terminal Donor–Acceptor Substitution, *Angew. Chem. Int. Ed.*, 2005, **44**, 2482-2506; b) S. Yao, H.-Y. Ahn, X. Wang, J. Fu, E. W. Van Stryland, D. J. Hagan and K. D. Belfield, Donor–Acceptor–Donor Fluorene Derivatives for Two-Photon Fluorescence Lysosomal Imaging, *J. Org. Chem.*, 2010, **75**, 3965-3974; c) C. D. Andrade, C. O. Yanez, L. Rodriguez and K. D. Belfield, A Series of Fluorene-Based Two-Photon Absorbing Molecules: Synthesis, Linear and Nonlinear Characterization, and Bioimaging, *J. Org. Chem.*, 2010, **75**, 3975-3982; d) D. R. Larson, W. R. Zipfel, R. M. Williams, S. W. Clark, M. P. Bruchez, F. W. Wise and W. W. Webb, Water-Soluble Quantum Dots for Multiphoton Fluorescence Imaging in Vivo, *Science*, 2003, **300**, 1434-1436; e) L. Ventelon, S. Charier, L. Moreaux, J. Mertz and M. Blanchard-Desce, Nanoscale push-push dihydrophenanthrene derivatives as novel fluorophores for two-photon-excited fluorescence, *Angew. Chem. Int. Ed.*, 2001, **40**, 2098-2101; f) T. R. Krishna, M. Parent, M. H. V. Werts, L. Moreaux, S. Gmouh, S. Charpak, A.-M. Caminade, J.-P. Majoral and M. Blanchard-Desce, Water-soluble dendrimeric two-photon tracers for in vivo imaging, *Angew. Chem. Int. Ed.*, 2006, **45**, 4645-4648; g) O. Mongin, T. R. Krishna, M. H. V. Werts, A.-M. Caminade, J.-P. Majoral and M. Blanchard-Desce, A modular approach to two-photon absorbing organic nanodots: brilliant dendrimers as an alternative to semiconductor quantum dots?, *Chem. Commun.*, 2006, 915-917; h) V. Parthasarathy, S. Fery-Forgues, E. Campioli, G. Recher, F. Terenziani and M. Blanchard-Desce, Dipolar versus Octupolar Triphenylamine-Based Fluorescent Organic Nanoparticles as Brilliant One- and Two-Photon Emitters for (Bio)imaging, *Small*, 2011, **7**, 3219-3229.
12. a) S. Kim, T. Y. Ohulchanskyy, H. E. Pudavar, R. K. Pandey and P. N. Prasad, Organically Modified Silica Nanoparticles Co-encapsulating Photosensitizing Drug and Aggregation-Enhanced Two-Photon Absorbing Fluorescent Dye Aggregates for Two-Photon Photodynamic Therapy, *J. Am. Chem. Soc.*, 2007, **129**, 2669-2675; b) K. Ogawa and Y. Kobuke, Design of two-photon absorbing materials for molecular optical memory and photodynamic therapy, *Org. Biomol. Chem.*, 2009, **7**, 2241-2246; c) C. B. Nielsen, J. Arnbjerg, M. Johnsen, M. Jørgensen and P. R. Ogilby, Molecular Tuning of Phenylene-Vinylene Derivatives for Two-Photon Photosensitized Singlet Oxygen Production, *J. Org. Chem.*, 2009, **74**, 9094-9104; d) J. R. Starkey, A. K. Rebane, M. A. Drobizhev, F. Meng, A. Gong, A. Elliott, K. McInnerney and C. W. Spangler, New Two-Photon Activated Photodynamic Therapy Sensitizers Induce Xenograft Tumor Regressions after Near-IR Laser Treatment through the Body of the Host Mouse, *Clin. Cancer Res.*, 2008, **14**, 6564-6573; e) H. A. Collins, M. Khurana, E. H. Moriyama, A. Mariampillai, E. Dahlstedt, M. Balaz, M. K. Kuimova, M. Drobizhev, V. X. D. Yang, D. Phillips, A. Rebane, B. C. Wilson and H. L. Anderson, Blood-vessel closure using photosensitizers engineered for two-photon excitation, *Nat. Photonics*, 2008, **2**, 420-424; f) M. Gary-Bobo, Y. Mir, C. Rouxel, D. Brevet, I. Basile, M. Maynadier, O. Vaillant, O. Mongin, M. Blanchard-Desce, A. Morère, M. Garcia, J.-O. Durand and L. Raehm, Mannose-Functionalized Mesoporous Silica Nanoparticles for Efficient Two-Photon Photodynamic Therapy of Solid Tumors, *Angew. Chem. Int. Ed.*, 2011, **50**, 11425-11429; g) M. Gary-Bobo, Y. Mir, C. Rouxel, D. Brevet, O. Hocine, M. Maynadier, A. Gallud, A. Da Silva, O. Mongin, M. Blanchard-Desce, S. Richeter, B. Looock, P. Maillard, A. Morere, M. Garcia, L. Raehm and J. O. Durand, Multifunctionalized mesoporous silica nanoparticles for the in vitro



- treatment of retinoblastoma: Drug delivery, one and two-photon photodynamic therapy, *Int. J. Pharm.*, 2012, **432**, 99-104.
13. a) L. Donato, A. Mourot, C. M. Davenport, C. Herbivo, D. Warther, J. Léonard, F. Bolze, J.-F. Nicoud, R. H. Kramer, M. Goeldner and A. Specht, Water-Soluble, Donor–Acceptor Biphenyl Derivatives in the 2-(o-Nitrophenyl)propyl Series: Highly Efficient Two-Photon Uncaging of the Neurotransmitter  $\gamma$ -Aminobutyric Acid at  $\lambda=800$  nm, *Angew. Chem. Int. Ed.*, 2012, **51**, 1840-1843; b) D. Warther, S. Gug, A. Specht, F. Bolze, J. F. Nicoud, A. Mourot and M. Goeldner, Two-photon uncaging: New prospects in neuroscience and cellular biology, *Bioorg. Med. Chem.*, 2010, **18**, 7753-7758; c) G. C. R. Ellis-Davies, Two-Photon Microscopy for Chemical Neuroscience, *ACS Chem. Neurosci.*, 2011, **2**, 185-197; d) G. C. R. Ellis-Davies, Caged compounds: photorelease technology for control of cellular chemistry and physiology, *Nat. Methods*, 2007, **4**, 619-628.
  14. a) D. A. Parthenopoulos and P. M. Rentzepis, Three-dimensional optical storage memory, *Science*, 1989, **245**, 843-845; b) C. C. Corredor, Z.-L. Huang, K. D. Belfield, A. R. Morales and M. V. Bondar, Photochromic Polymer Composites for Two-Photon 3D Optical Data Storage, *Chem. Mater.*, 2007, **19**, 5165-5173.
  15. a) P.-A. Bouit, G. Wetzels, G. Berginc, B. Loiseaux, L. Toupet, P. Feneyrou, Y. Bretonnière, K. Kamada, O. Maury and C. Andraud, Near IR Nonlinear Absorbing Chromophores with Optical Limiting Properties at Telecommunication Wavelengths, *Chem. Mater.*, 2007, **19**, 5325-5335; b) Q. Zheng, G. S. He and P. N. Prasad, A novel near IR two-photon absorbing chromophore: Optical limiting and stabilization performances at an optical communication wavelength, *Chem. Phys. Lett.*, 2009, **475**, 250-255; c) G. S. He, G. C. Xu, P. N. Prasad, B. A. Reinhardt, J. C. Bhatt, R. McKellar and A. G. Dillard, Two-photon absorption and optical-limiting properties of novel organic compounds, *Opt. Lett.*, 1995, **20**, 435-437; d) J. E. Ehrlich, X. L. Wu, I. Y. S. Lee, Z. Y. Hu, H. Röckel, S. R. Marder and J. W. Perry, Two-photon absorption and broadband optical limiting with bis-donor stilbenes, *Opt. Lett.*, 1997, **22**, 1843-1845; e) M. Charlot, N. Izard, O. Mongin, D. Riehl and M. Blanchard-Desce, Optical limiting with soluble two-photon absorbing quadrupoles: Structure-property relationships, *Chem. Phys. Lett.*, 2006, **417**, 297-302; f) G. Lemerrier, J.-C. Mulatier, C. Martineau, R. Anémian, C. Andraud, I. Wang, O. Stéphan, N. Amari and P. Baldeck, Two-photon absorption: from optical power limiting to 3D microfabrication, *C. R. Chimie*, 2005, **8**, 1308-1316.
  16. a) S. Maruo, O. Nakamura and S. Kawata, Three-dimensional microfabrication with two-photon-absorbed photopolymerization, *Opt. Lett.*, 1997, **22**, 132-134; b) S. Kawata, H.-B. Sun, T. Tanaka and K. Takada, Finer features for functional microdevices, *Nature*, 2001, **412**, 697-698; c) W. Zhou, S. M. Kuebler, K. L. Braun, T. Yu, J. K. Cammack, C. K. Ober, J. W. Perry and S. R. Marder, An efficient two-photon-generated photoacid applied to positive-tone 3D microfabrication, *Science*, 2002, **296**, 1106-1109; d) F. Claeysens, E. A. Hasan, A. Gaidukeviciute, D. S. Achilleos, A. Ranella, C. Reinhardt, A. Ovsianikov, X. Shizhou, C. Fotakis, M. Vamvakaki, B. N. Chichkov and M. Farsari, Three-Dimensional Biodegradable Structures Fabricated by Two-Photon Polymerization, *Langmuir*, 2009, **25**, 3219-3223; e) I. Sakellari, E. Kabouraki, D. Gray, V. Purlys, C. Fotakis, A. Pikulin, N. Bityurin, M. Vamvakaki and M. Farsari, Diffusion-Assisted High-Resolution Direct Femtosecond Laser Writing, *Acs Nano*, 2012, **6**, 2302-2311.
  17. a) L. Ventelon, L. Moreaux, J. Mertz and M. Blanchard-Desce, New quadrupolar fluorophores with high two-photon excited fluorescence, *Chem. Commun.*, 1999, 2055-2056; b) O. Mongin, L. Porrès, L. Moreaux, J. Mertz and M. Blanchard-Desce,

- Synthesis and Photophysical Properties of New Conjugated Fluorophores Designed for Two-Photon-Excited Fluorescence, *Org. Lett.*, 2002, **4**, 719-722; c) L. Porrès, O. Mongin, C. Katan, M. Charlot, T. Pons, J. Mertz and M. Blanchard-Desce, Enhanced Two-Photon Absorption with Novel Octupolar Propeller-Shaped Fluorophores Derived from Triphenylamine, *Org. Lett.*, 2004, **6**, 47-50; d) C. Le Droumaguet, O. Mongin, M. H. V. Werts and M. Blanchard-Desce, Towards "smart" multiphoton fluorophores: strongly solvatochromic probes for two-photon sensing of micropolarity, *Chem. Commun.*, 2005, 2802-2804; e) M. H. V. Werts, S. Gmouh, O. Mongin, T. Pons and M. Blanchard-Desce, Strong Modulation of Two-Photon Excited Fluorescence of Quadripolar Dyes by (De)Protonation, *J. Am. Chem. Soc.*, 2004, **126**, 16294-16295; f) M. G. Silly, L. Porrès, O. Mongin, P.-A. Chollet and M. Blanchard-Desce, Optical limiting in the red-NIR range with soluble two-photon absorbing molecules, *Chem. Phys. Lett.*, 2003, **379**, 74-80; g) O. Mongin, L. Porrès, M. Charlot, C. Katan and M. Blanchard-Desce, Synthesis, Fluorescence, and Two-Photon Absorption of a Series of Elongated Rodlike and Banana-shaped Quadripolar Fluorophores: A Comprehensive Study of Structure-Property Relationships, *Chem. Eur. J.*, 2007, **13**, 1481-1498; h) O. Mongin, A. Pla-Quintana, F. Terenziani, D. Drouin, C. Le Droumaguet, A.-M. Caminade, J.-P. Majoral and M. Blanchard-Desce, Organic nanodots for multiphotonics: synthesis and photophysical studies, *New J. Chem.*, 2007, **31**, 1354-1367; i) O. Mongin, C. Rouxel, A.-C. Robin, A. Pla-Quintana, T. Rama Krishna, G. Recher, F. Tiaho, A.-M. Caminade, J.-P. Majoral and M. Blanchard-Desce, Brilliant organic nanodots: novel nano-objects for bionanophotonics, *Proc. SPIE*, 2008, **7040**, 704006; j) M. Guo, O. Varnavski, A. Narayanan, O. Mongin, J.-P. Majoral, M. Blanchard-Desce and T. Goodson, Investigations of Energy Migration in an Organic Dendrimer Macromolecule for Sensory Signal Amplification, *J. Phys. Chem. A*, 2009, **113**, 4763-4771; k) O. Mongin, C. Rouxel, J.-M. Vabre, Y. Mir, A. Pla-Quintana, Y. Wei, A.-M. Caminade, J.-P. Majoral and M. Blanchard-Desce, Customized multiphotonics nanotools for bioapplications: soft organic nanodots as an eco-friendly alternative to quantum dots *Proc. SPIE*, 2009, **7403**, 740303; l) A. Rebane, M. Drobizhev, N. S. Makarov, E. Beuerman, J. E. Haley, M. K. Douglas, A. R. Burke, J. L. Flikkema and T. M. Cooper, Relation between Two-Photon Absorption and Dipolar Properties in a Series of Fluorenyl-Based Chromophores with Electron Donating or Electron Withdrawing Substituents, *J. Phys. Chem. A*, 2011, **115**, 4255-4262.
18. a) C. Herbivo, A. Comel, G. Kirsch and M. M. M. Raposo, Synthesis of 5-aryl-5'-formyl-2,2'-bithiophenes as new precursors for nonlinear optical (NLO) materials, *Tetrahedron*, 2009, **65**, 2079-2086; b) M. M. M. Raposo, M. C. R. Castro, M. Belsley and A. M. C. Fonseca, Push pull bithiophene azo-chromophores bearing thiazole and benzothiazole acceptor moieties: Synthesis and evaluation of their redox and nonlinear optical properties, *Dyes Pigments*, 2011, **91**, 454-465.
19. a) Y.-S. Yen, W.-T. Chen, C.-Y. Hsu, H.-H. Chou, J. T. Lin and M.-C. P. Yeh, Arylamine-Based Dyes for p-Type Dye-Sensitized Solar Cells, *Org. Lett.*, 2011, **13**, 4930-4933; b) F. Zhang, Y.-h. Luo, J.-s. Song, X.-z. Guo, W.-l. Liu, C.-p. Ma, Y. Huang, M.-f. Ge, Z. Bo and Q.-B. Meng, Triphenylamine-based dyes for dye-sensitized solar cells, *Dyes Pigments*, 2009, **81**, 224-230; c) E. Ripaud, Y. Olivier, P. Leriche, J. Cornil and J. Roncali, Polarizability and Internal Charge Transfer in Thiophene-Triphenylamine Hybrid pi-Conjugated Systems, *J. Phys. Chem. B*, 2011, **115**, 9379-9386; d) P. Leriche, P. Frere, A. Cravino, O. Aleveque and J. Roncali, Molecular engineering of the internal charge transfer in thiophene-triphenylamine hybrid pi-conjugated systems, *J. Org. Chem.*, 2007, **72**, 8332-8336; e) A. Leliège, P.

- Blanchard, T. o. Rousseau and J. Roncali, Triphenylamine/Tetracyanobutadiene-Based D-A-D  $\pi$ -Conjugated Systems as Molecular Donors for Organic Solar Cells, *Org. Lett.*, 2011, **13**, 3098-3101; f) Q. Bricaud, A. Cravino, P. Leriche and J. Roncali, Terthiophene-cyanovinylene  $\pi$ -conjugated polymers as donor material for organic solar cells, *Synthetic Met.*, 2009, **159**, 2534-2538.
20. a) T. Narita, M. Takase, T. Nishinaga, M. Iyoda, K. Kamada and K. Ohta, Star-Shaped Oligothiophenes with Unique Photophysical Properties and Nanostructured Polymorphs, *Chem. Eur. J.*, 2010, **16**, 12108-12113; b) S. Ellinger, K. R. Graham, P. Shi, R. T. Farley, T. T. Steckler, R. N. Brookins, P. Taranekar, J. Mei, L. A. Padilha, T. R. Ensley, H. Hu, S. Webster, D. J. Hagan, E. W. Van Stryland, K. S. Schanze and J. R. Reynolds, Donor–Acceptor–Donor-based  $\pi$ -Conjugated Oligomers for Nonlinear Optics and Near-IR Emission, *Chem. Mater.*, 2011, **23**, 3805-3817.
  21. X. J. Feng, P. L. Wu, H. L. Tam, K. F. Li, M. S. Wong and K. W. Cheah, Fluorene-Based  $\pi$ -Conjugated Oligomers for Efficient Three-Photon Excited Photoluminescence and Lasing, *Chem. Eur. J.*, 2009, **15**, 11681-11691.
  22. V. Alain, L. Thouin, M. Blanchard-Desce, U. Gubler, C. Bosshard, P. Günter, J. Müller, A. Fort and M. Barzoukas, Molecular Engineering of Push–Pull Phenylpolyenes for Nonlinear Optics: Improved Solubility, Stability, and Nonlinearities, *Adv. Mater.*, 1999, **11**, 1210-1214.
  23. a) M. Blanchard-Desce, V. Alain, L. Midrier, R. Wortmann, S. Lebus, C. Glania, P. Krämer, A. Fort, J. Müller and M. Barzoukas, Intramolecular charge transfer and enhanced quadratic optical non-linearities in push pull polyenes, *J. Photochem. Photobiol. A: Chem.*, 1997, **105**, 115-121; b) W. Akemann, D. Laage, P. Plaza, M. M. Martin and M. Blanchard-Desce, Photoinduced Intramolecular Charge Transfer in Push–Pull Polyenes: Effects of Solvation, Electron-Donor Group, and Polyenic Chain Length†, *J. Phys. Chem. B*, 2008, **112**, 358-368; c) M. Blanchard-Desce, R. Wortmann, S. Lebus, J.-M. Lehn and P. Krämer, Intramolecular charge transfer in elongated donor-acceptor conjugated polyenes, *Chem. Phys. Lett.*, 1995, **243**, 526-532; d) D. Laage, P. Plaza, M. Blanchard-Desce and M. M. Martin, Multiple relaxation pathways in push-pull polyenes, *Photochem. Photobiol. Sci.*, 2002, **1**, 526-535.
  24. a) M. Barzoukas, C. Runser, A. Fort and M. Blanchard-Desce, A two-state description of (hyper) polarizabilities of push-pull molecules based on a two-form model, *Chem. Phys. Lett.*, 1996, **257**, 531; b) M. Barzoukas and M. Blanchard-Desce, Molecular engineering of push-pull dipolar and quadrupolar molecules for two-photon absorption: A multivalence-bond states approach, *J. Chem. Phys.*, 2000, **113**, 3951-3959.
  25. S. J. Strickler and R. A. Berg, Relation between absorption intensity and fluorescence lifetime of molecules, *J. Chem. Phys.*, 1962, **37**, 814-822.
  26. a) C. Xu and W. W. Webb, Measurement of two-photon excitation cross sections of molecular fluorophores with data from 690 to 1050 nm, *J. Opt. Soc. Am. B*, 1996, **13**, 481-491; b) M. A. Albota, C. Xu and W. W. Webb, Two-photon fluorescence excitation cross sections of biomolecular probes from 690 to 960 nm, *Appl. Opt.*, 1998, **37**, 7352-7356.
  27. A. Rebane, M. A. Drobizhev, N. S. Makarov, E. Beuerman, C. Nacke and J. Pahapill, Modeling non-Lorentzian two-photon absorption line shape in dipolar chromophores, *J. Lumin.*, 2010, **130**, 1055-1059.
  28. Y. M. Poronik, V. Hugues, M. Blanchard-Desce and D. T. Gryko, Octupolar Merocyanine Dyes: A New Class of Nonlinear Optical Chromophores, *Chem. Eur. J.*, 2012, **18**, 9258-9266.

29. A. M. Brouwer, Standards for photoluminescence quantum yield measurements in solution (IUPAC Technical Report), *Pure Appl. Chem.*, 2011, **83**, 2213–2228.
30. M. H. V. Werts, N. Nerambourg, D. Pélégry, Y. Le Grand and M. Blanchard-Desce, Action cross sections of two-photon excited luminescence of some Eu(III) and Tb(III) complexes, *Photochem. Photobiol. Sci.*, 2005, **4**, 531-538.
31. C. Katan, S. Tretiak, M. H. V. Werts, A. J. Bain, R. J. Marsh, N. Leonczek, N. Nicolaou, E. Badaeva, O. Mongin and M. Blanchard-Desce, Two-Photon Transitions in Quadrupolar and Branched Chromophores: Experiment and Theory, *J. Phys. Chem. B*, 2007, **111**, 9468-9483.


**Table 1.** Photophysical properties of compounds **1-6** in chloroform solution

	D	A	$\pi$	$\lambda_{\text{abs}}^{\text{max}}$ (nm)	$\text{Log } \epsilon^{\text{max}}$ ( $\text{M}^{-1} \cdot \text{cm}^{-1}$ )	FWHM ( $10^3 \text{ cm}^{-1}$ )	$\lambda_{\text{em}}^{\text{max}}$ (nm)	Stokes shift ( $10^3 \text{ cm}^{-1}$ )	$\Phi_{\text{f}}$ (%)	$\tau$ (ns)	$k_{\text{r}}$ ( $10^8 \text{ s}^{-1}$ )	$k_{\text{nr}}$ ( $10^9 \text{ s}^{-1}$ )
<b>1a</b>	H	CHO	Ph-Thien	331	4.35	4.6	375	3.6	0.4	-	-	-
<b>1b</b>	OMe	CHO	Ph-Thien	352	4.34	4.6	427	5.0	13.7	0.6	2.3	1.41
<b>1d</b>	NMe <sub>2</sub>	CHO	Ph-Thien	408	4.45	4.3	507	4.8	84.5	2.9	2.9	0.06
<b>2a</b>	H	CH=C(CN) <sub>2</sub>	Ph-Thien	404	4.54	3.8	443	2.2	0.04	-	-	-
<b>2b</b>	OMe	CH=C(CN) <sub>2</sub>	Ph-Thien	431	4.56	3.9	502	3.3	0.2	-	-	-
<b>2c</b>	OEt	CH=C(CN) <sub>2</sub>	Ph-Thien	433.5	4.54	3.9	502	3.2	0.2	-	-	-
<b>2d</b>	NMe <sub>2</sub>	CH=C(CN) <sub>2</sub>	Ph-Thien	511.5	4.55	3.5	609	3.1	13.5	0.6	2.1	1.37
<b>3a</b>	H	CHO	Ph-(Thien) <sub>2</sub>	390.5	4.39	4.4	469	4.3	35	1.2	3.0	0.55
<b>3c</b>	OEt	CHO	Ph-(Thien) <sub>2</sub>	403	4.38	4.5	505	5.0	79	2.5	3.2	0.09
<b>3d</b>	NMe <sub>2</sub>	CHO	Ph-(Thien) <sub>2</sub>	437.5	4.45	4.8	601	6.2	77	3.4	2.3	0.07
<b>3e</b>	NEt <sub>2</sub>	CHO	Ph-(Thien) <sub>2</sub>	448.5	4.40	4.6	612	6.0	74	3.4	2.2	0.08
<b>4a</b>	H	CH=C(CN) <sub>2</sub>	Ph-(Thien) <sub>2</sub>	468	4.59	3.8	546	3.0	0.5	-	-	-
<b>4c</b>	OEt	CH=C(CN) <sub>2</sub>	Ph-(Thien) <sub>2</sub>	486.5	4.61	3.9	599	3.9	5	0.4	1.4	2.64
<b>4e</b>	NEt <sub>2</sub>	CH=C(CN) <sub>2</sub>	Ph-(Thien) <sub>2</sub>	551.5	4.59	4.0	727	4.4	34	2.7	1.2	0.24
<b>5a</b>	H	DET <sub>B</sub>	Ph-Thien	464.5	4.71	3.2	524	2.4	0.04	-	-	-
<b>5b</b>	OMe	DET <sub>B</sub>	Ph-Thien	491.5	4.74	3.2	555	2.3	0.1	-	-	-
<b>5c</b>	OEt	DET <sub>B</sub>	Ph-Thien	494	4.72	3.2	561	2.4	0.2	-	-	-
<b>5d</b>	NMe <sub>2</sub>	DET <sub>B</sub>	Ph-Thien	571.5	4.79	2.9	669	2.6	8.7	0.4	0.22	2.28
<b>6a</b>	H	DET <sub>B</sub>	Ph-(Thien) <sub>2</sub>	526.5	4.72	3.2	596	2.2	0.5	-	-	-
<b>6b</b>	OMe	DET <sub>B</sub>	Ph-(Thien) <sub>2</sub>	541	4.74	3.3	644	3.0	8.8	0.2	0.44	4.56
<b>6d</b>	NMe <sub>2</sub>	DET <sub>B</sub>	Ph-(Thien) <sub>2</sub>	587.5	4.66	3.8	781	4.2	5.6	1.1	0.05	0.84


**Table 2.** TPA properties of compounds **1-6** in chloroform solution

	D	A	$\pi$	$2\lambda_{ICT}$ (nm)	$\lambda_{TPA}^{max1}$ (nm)	$\sigma_2$ (GM) at $\lambda_{TPA}^{max1}$	$\lambda_{TPA}$ (nm)
<b>1b</b>	OMe	CHO	Ph-Thien	704	730	56	
<b>1d</b>	NMe <sub>2</sub>	CHO	Ph-Thien	816	820	124	
<b>2a</b>	H	CH=C(CN) <sub>2</sub>	Ph-Thien	808	820	28	
<b>2b</b>	OMe	CH=C(CN) <sub>2</sub>	Ph-Thien	862	880	95	
<b>2c</b>	OEt	CH=C(CN) <sub>2</sub>	Ph-Thien	867	880	108	
<b>2d</b>	NMe <sub>2</sub>	CH=C(CN) <sub>2</sub>	Ph-Thien	1023	1050	176	
<b>3a</b>	H	CHO	Ph-(Thien) <sub>2</sub>	781	770	47	
<b>3c</b>	OEt	CHO	Ph-(Thien) <sub>2</sub>	806	820	115	
<b>3d</b>	NMe <sub>2</sub>	CHO	Ph-(Thien) <sub>2</sub>	875	890	208	
<b>3e</b>	NEt <sub>2</sub>	CHO	Ph-(Thien) <sub>2</sub>	897	890	253	
<b>4c</b>	OEt	CH=C(CN) <sub>2</sub>	Ph-(Thien) <sub>2</sub>	973	930 1040	210 125	
<b>4e</b>	NEt <sub>2</sub>	CH=C(CN) <sub>2</sub>	Ph-(Thien) <sub>2</sub>	1103	1100 1190	570 600	7
<b>5d</b>	NMe <sub>2</sub>	DET <sub>B</sub>	Ph-Thien	1143	1120	428	8
<b>6d</b>	NMe <sub>2</sub>	DET <sub>B</sub>	Ph-(Thien) <sub>2</sub>	1175	> 1170 1100	> 1600 1180	


- Not determined due to excitation and fluorescence wavelengths overlap

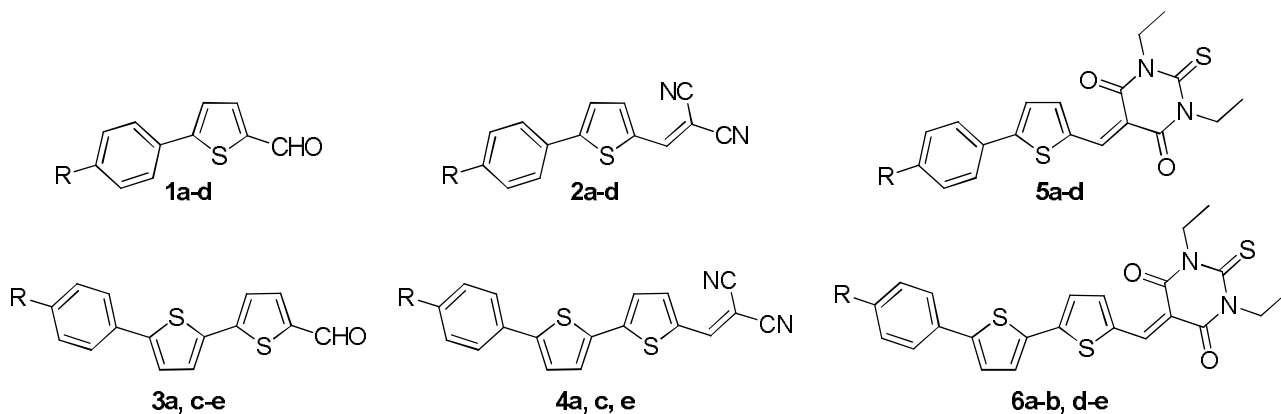



a: R = H; b: R = MeO; c: R = EtO; d: R = NMe<sub>2</sub>; e: R = NEt<sub>2</sub>

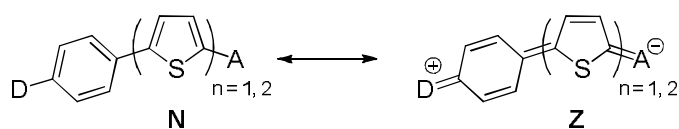

**Scheme 1** Structure of compounds **1-6** and the neutral (N) and zwitterionic (Z) limiting-resonance forms.

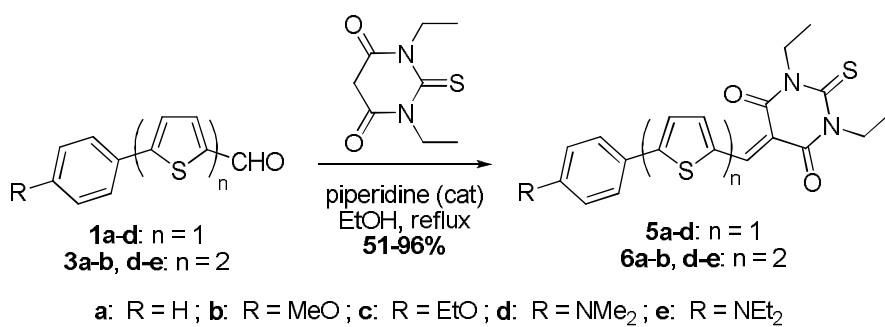


**Scheme 2** Synthesis of thiobarbituric acid derivatives **5** and **6**.

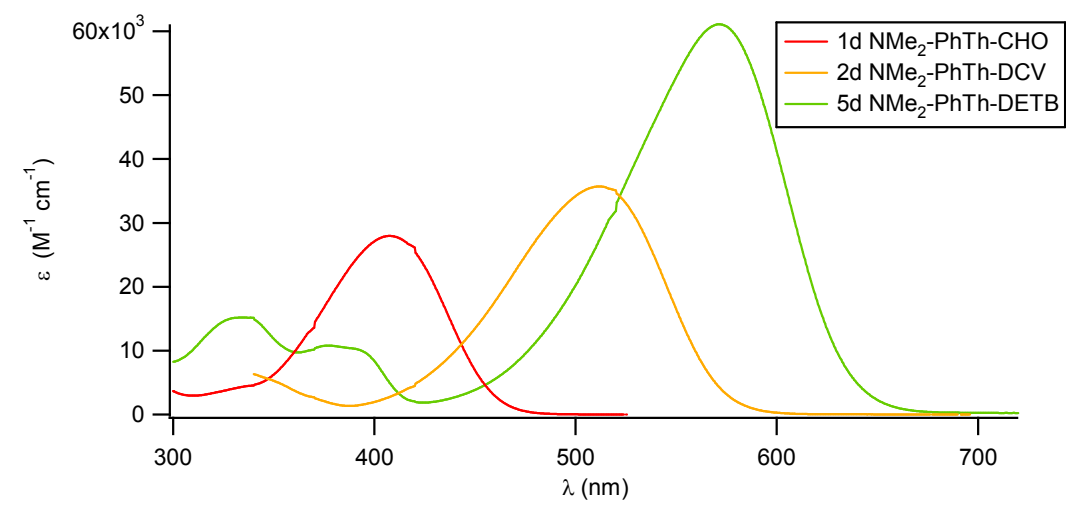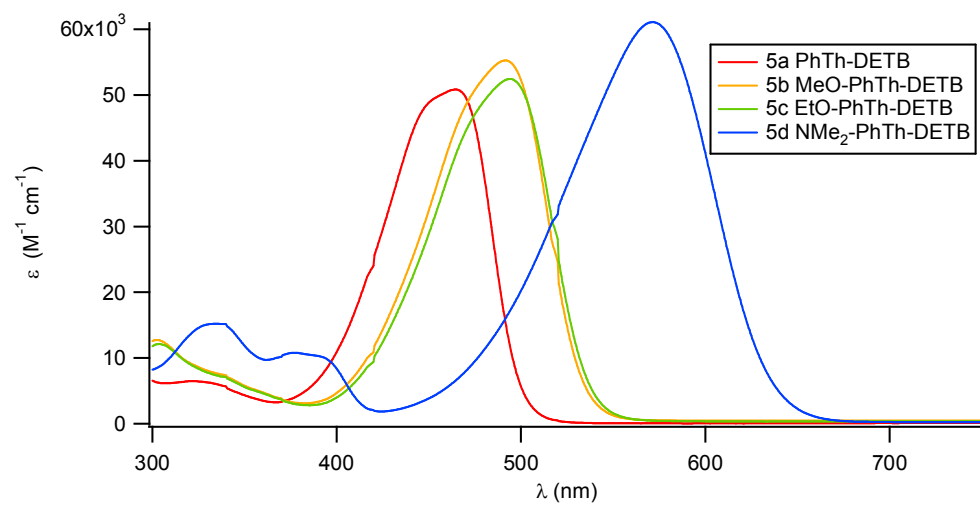


**Figure 1.** UV-vis absorption spectra of compounds **5a-d** and **1,2,5d**: end-groups effect (donor strength: left and acceptor strength: right)




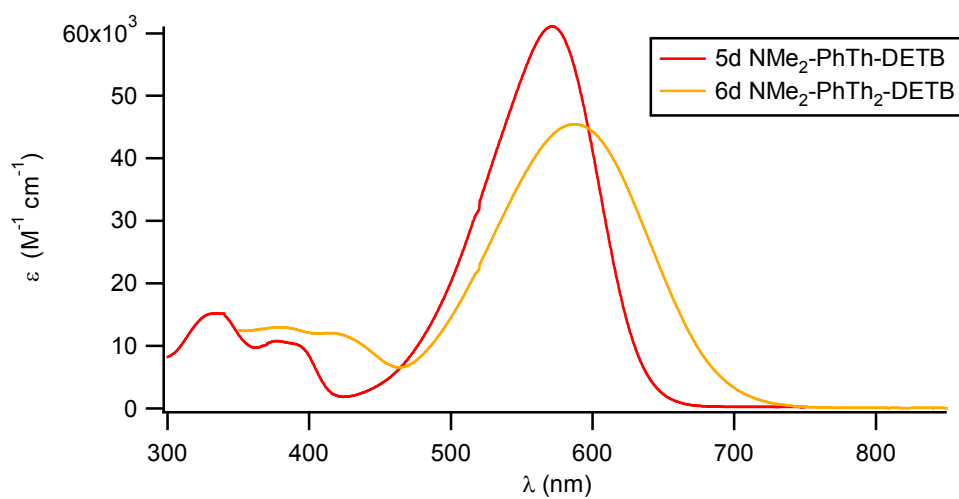


**Figure 2.** UV-vis absorption spectra of push-pull compounds **5-6,d**: effect of  $\pi$ -connector length.

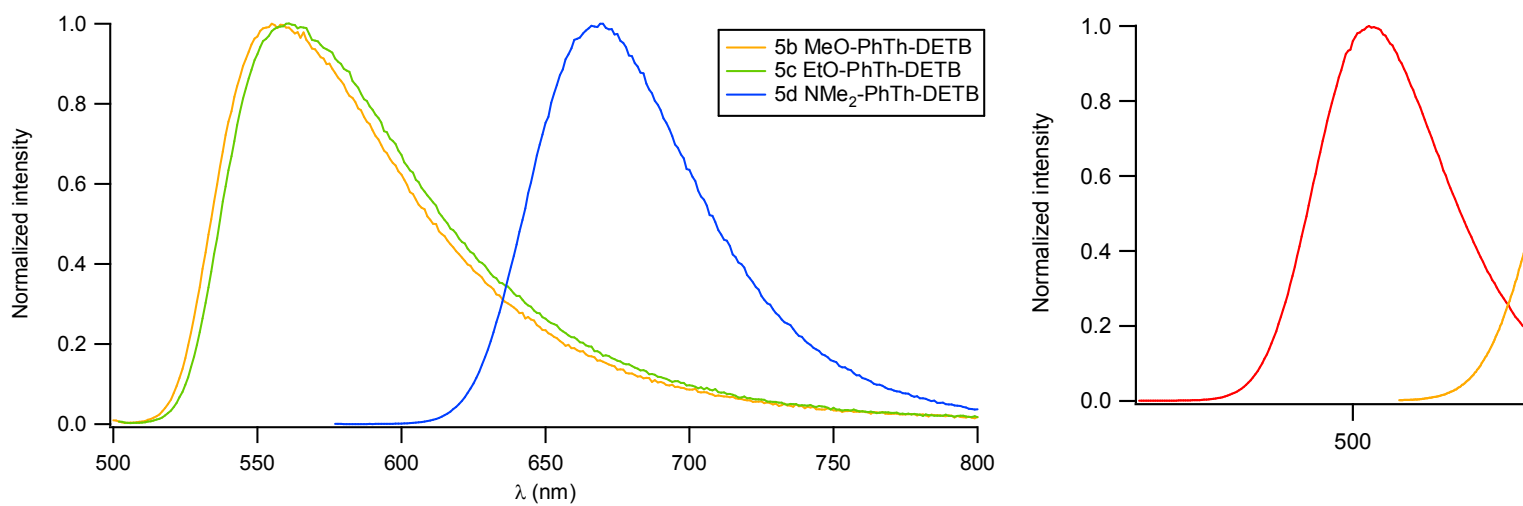



**Figure 3.** Fluorescence emission spectra of push-pull compounds **5b-d** and **1,2,5d**: end-groups effect (donor str

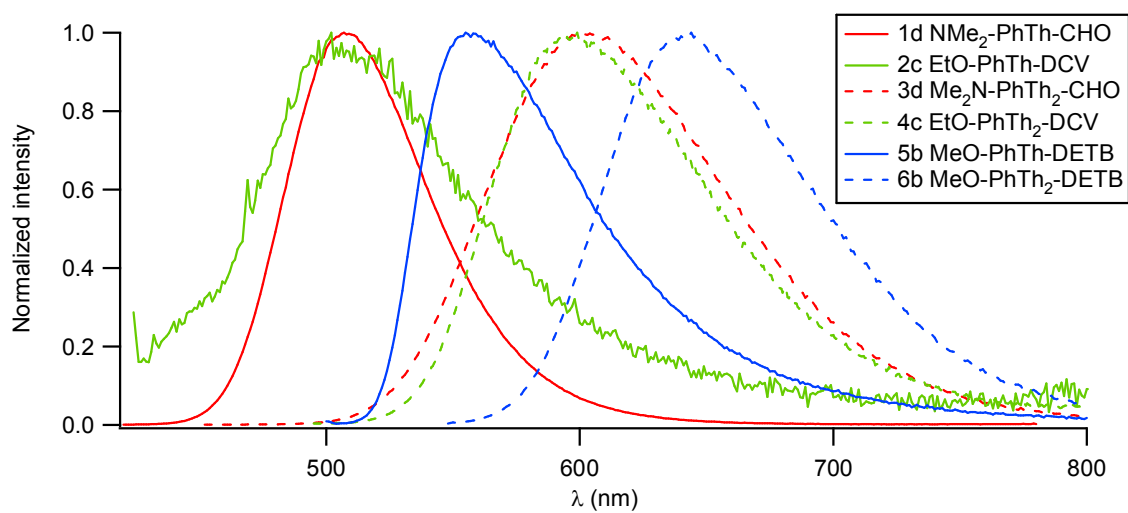

**Figure 4.** . Fluorescence emission spectra of push-pull compounds **1,3d**; **2,4c** and **5-6c**: length effect.

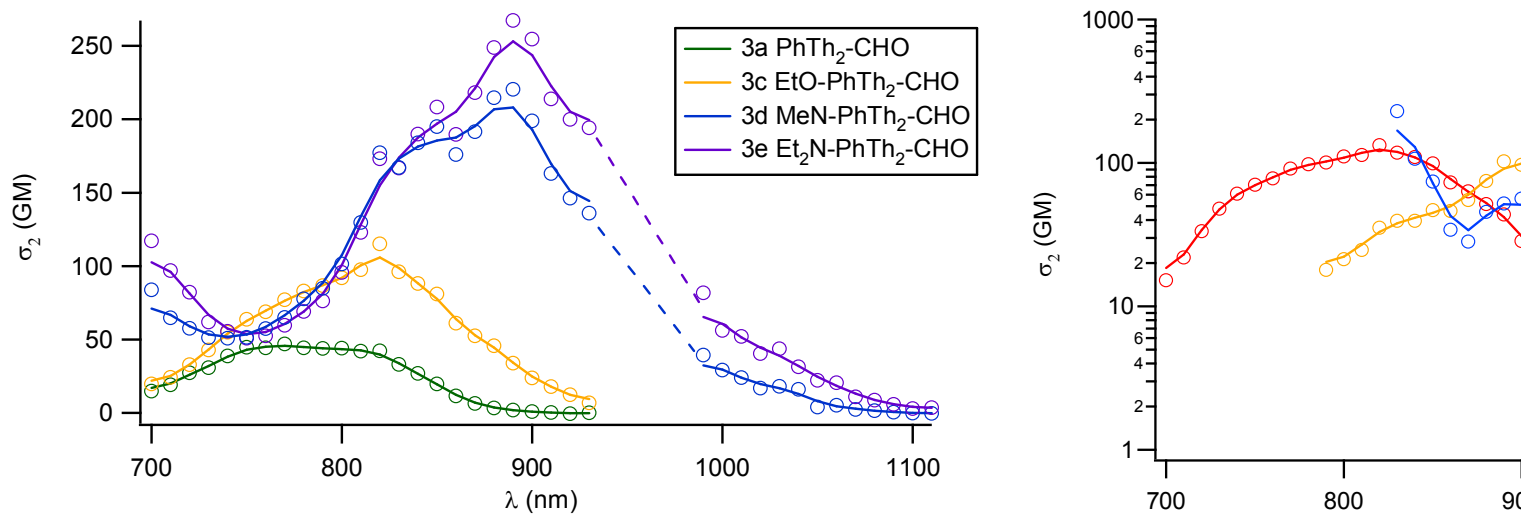

**Figure 5.** Two-photon absorption spectra of compounds **3a-e** and **1,2,5d**: end-groups effect (donor strength: left

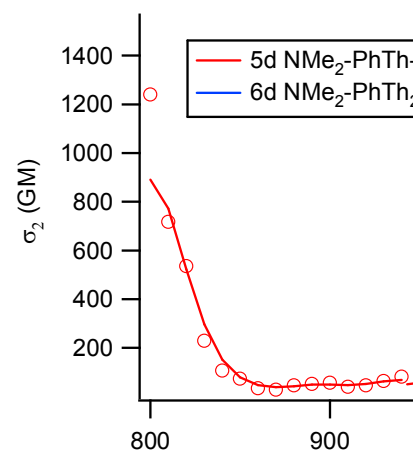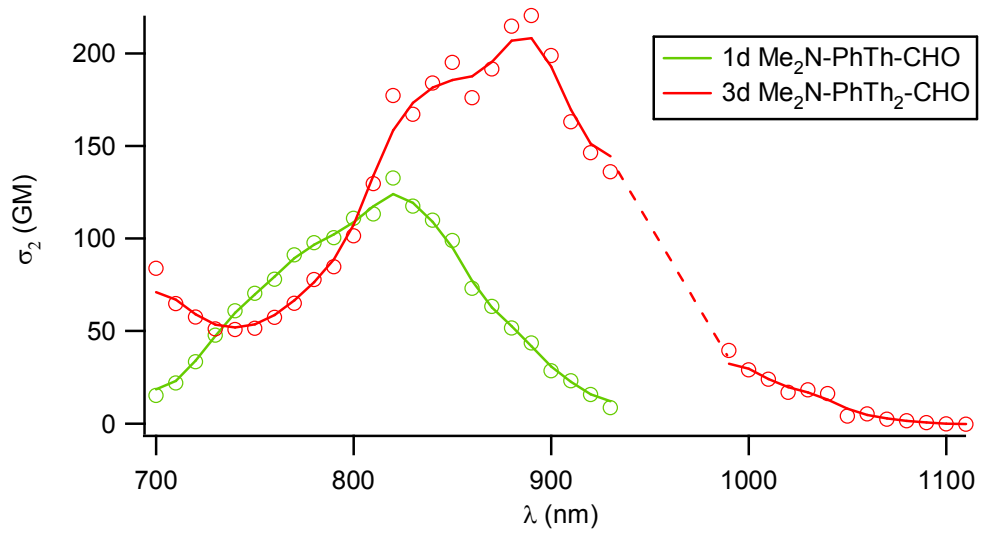

**Figure 6.** Two-photon absorption spectra of compounds **1,3d** and **5-6d**: length effect.